

HERCULUX Chengdu HercuLux Photoelectric 恒坤光电 Technology Co. Ltd. Technology Co.,Ltd

Product Approval


Approval number:


Customer:

Manufacturer: Chengdu HercuLux Photoelectric Technology Co.,Ltd

PN	Code	Product
HK-28@14-15-D4-21-1g-1	1. 01. 91835	HK 28@14-15°lens
HK-28@14-24-D4-21-1g-1	1. 01. 91836	HK 28@14-24°1ens
HK-28@14-36-D4-21-1g-1	1. 01. 91840	HK 28@14-36°lens
HK-28@14-50-D4-21-1g-1	1. 01. 02343	HK 28@14-50°1ens

Synthetic information: 1.07.81418_HK-166@03-0223-S

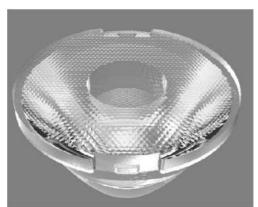



	Supplier co	onfirmation	Client confirmation					
Proposed		DATE	Qualified□		D.A.T.F.			
Project manager		DATE	Unqualified □ D.		DATE			
Audit		DATE	Audit		DATE			
Approved		DATE	Approved		DATE			
Stamp		DATE	Stamp		DATE			

(Confirmation of acceptance by both parties must be signed and sealed)

Factory: Chengdu Shuangliu District, Iot industrial park 2 road HercuLux Photoelectric Park

Phone: 028-85887727 (801) 028-85887990 (801) Fax: 028-85887730 http://www.herculux.cn/ Sales Dept: Shenzhen Nanshan District Nanshan Cloud Valley Innovation Industrial Park Comprehensive Service Building,

TEL: 0755-2937 1541 FAX: 0755-2907 5140

*Approval In duplicate, for both supplier and customer.




HERCULUX Product Approval

TEL: 0755-2937 1541 Date updated: 2021/5/7 FAX: 0755-2907 5140 http://www.herculux.cn/

Product Picture:	
PN:	HK-28@14-15-D4-21-1g-1
Size(L*W*H/Φ*H):	Ф:28mm; H:14.3mm
Material:	PC
Effiency:	\
Temperature(Topr):	Material extreme temperature resistance : -40°C to +120°C long-term use temperature : -40°C to +90°C
FWHM:	15°、24°、36°
Matched LES:	LED D4



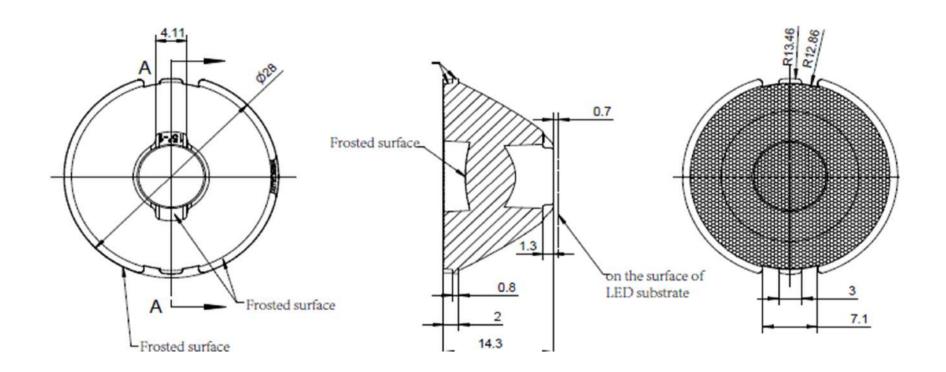


- 1. The 3D map is not indicated for rounded corners and draft angle.
- 2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
- 3, The surface has no flash, shrinkage, bubbles and other defects.

Opti	ical	design							HK-28@14-15-D4-21-1g-1					
truc	ture	e desig				HK 28	8@14-15ºlens			1.01.91835				
F	Revi	iew						umber o	f drawin	qty	we	ight		
Va	Validation				Material:	PC		CDHK						

MT5 Tolerance	Basic size	<3	3∼10	24~65	65~140	140~250	250~	450 >	450				
	olerance valu	±0.1	±0.15	±0.35	±0.50	±0.80	±1.2	2 ±	2.0				




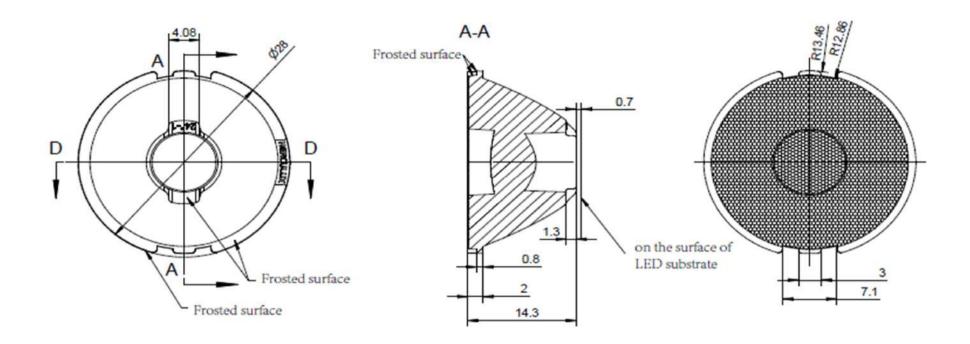

- 1. The 3D map is not indicated for rounded corners and draft angle.
- 2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
- 3, The surface has no flash, shrinkage, bubbles and other defects.

C	ptical	design								HK-28@14-24-D4-21-1g-1						
iti	tructure desig						HK 28	HK 28@14-24ºlens			1.01.91836					
	Revi	iew						umber o	f drawin	qty	we	ight				
	Validation				Material:	PC		CDHK								




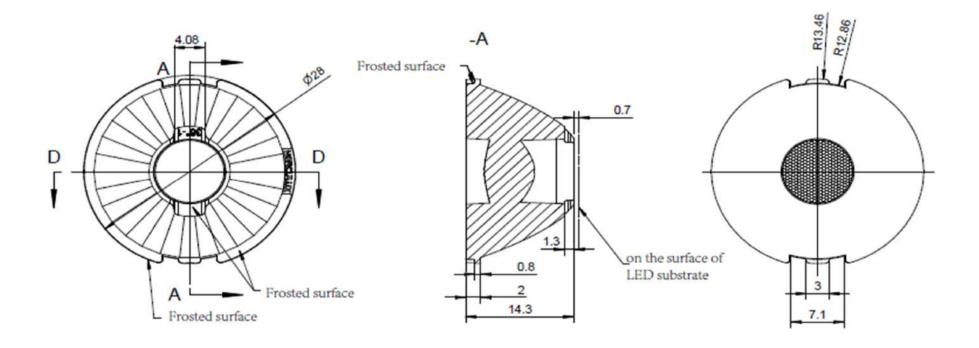

- 1. The 3D map is not indicated for rounded corners and draft angle.
- 2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
- 3, The surface has no flash, shrinkage, bubbles and other defects.

Opti	ical	design							HK-28@14-36-D4-21-1g-1						
truc	ture	e desig				HK 28	8@14-36ºlens			1.01.91840					
F	Revi	ew						umber o	f drawin	qty	we	ight			
Va	Validation				Material:	PC	CDHK								



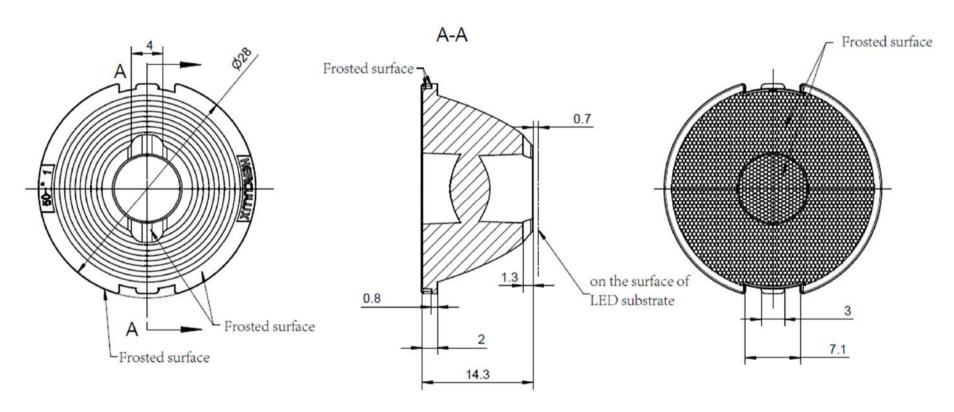



- 1. The 3D map is not indicated for rounded corners and draft angle.
- 2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
- 3, The surface has no flash, shrinkage, bubbles and other defects.

Optical design				HK-28@14-50-D4-21-1g-1						
tructure desig		HK 28	3@14-50ºlens	1.01.02343						
Review				umber of drawin	umber of drawin qty we					
Validation		Material:	#N/A		-					

										 •		
MT5 Tolerance	Basic size	<3	3∼10	24~65	65~140	140~250	250~450	>450				
	olerance valu	±0.1	±0.15	±0.35	±0.50	±0.80	±1.2	±2.0)			







Intensity data: (deg , cd) C0-180

λ	1	λ	I	λ	I	λ	1	λ	1	λ	1
-90.0	0.3729	-58.5	6.050	-27.0	63.63	4.5	2280	36.0	19.65	67.5	2.816
-88.5	0.3959	-57.0	6.814	-25.5	81.69	6.0	1876	37.5	17.44	69.0	2.578
-87.0	0.6228	-55.5	7.558	-24.0	106.8	7.5	1479	39.0	15.61	70.5	2.338
-85.5	0.8363	-54.0	8.292	-22.5	142.1	9.0	1144	40.5	14.15	72.0	2.169
-84.0	0.9292	-52.5	9.079	-21.0	186.0	10.5	875.5	42.0	12.98	73.5	1.927
-82.5	1.154	-51.0	9.808	-19.5	243.5	12.0	666.5	43.5	12.06	75.0	1.742
-81.0	1.312	-49.5	10.53	-18.0	318.6	13.5	505.9	45.0	11.26	76.5	1.604
-79.5	1.440	-48.0	11.22	-16.5	412.2	15.0	380.8	46.5	10.59	78.0	1.436
-78.0	1.611	-46.5	11.90	-15.0	529.7	16.5	279.3	48.0	9.892	79.5	1.283
-76.5	1.823	-45.0	12.66	-13.5	681.2	18.0	210.7	49.5	9.104	81.0	1.179
-75.0	2.017	-43.5	13.57	-12.0	881.4	19.5	157.9	51.0	8.428	82.5	1.000
-73.5	2.243	-42.0	14.61	-10.5	1149	21.0	119.3	52.5	7.703	84.0	0.9334
-72.0	2.459	-40.5	16.08	-9.0	1491	22.5	91.95	54.0	7.042	85.5	0.7710
-70.5	2.685	-39.0	17.81	-7.5	1892	24.0	72.62	55.5	6.337	87.0	0.7118
-69.0	2.922	-37.5	19.85	-6.0	2296	25.5	58.66	57.0	5.720	88.5	0.7534
-67.5	3.167	-36.0	22.53	-4.5	2613	27.0	48.50	58.5	5.178	90.0	0.7355
-66.0	3.497	-34.5	25.71	-3.0	2789	28.5	40.69	60.0	4.589		
-64.5	3.875	-33.0	29.62	-1.5	2835	30.0	34.62	61.5	4.110		
-63.0	4.316	-31.5	34.68	0.0	2849	31.5	29.57	63.0	3.718		
-61.5	4.842	-30.0	41.32	1.5	2788	33.0	25.60	64.5	3.362		J.
-60.0	5.417	-28.5	50.66	3.0	2597	34.5	22.27	66.0	3.033		

Electricity Parameter:

Current I: 0.1000A Power: 3.420W Voltage V: 34.20V PF: 1.000


Optical Parameter (Distance=2.410m):


Diffuse angle: @(25%): 24.8deg@(50%): 16.9deg@(75%): 11.6deg@(50%): 16.9deg
Diffuse angle: @(25%): 24.8deg@(50%): 16.9deg@(75%): 11.6deg@(50%): 16.9deg
Imax=2849cd (C=0.0deg, C=0.0deg)

CO-180Plane Imax= 2849cd (C=0.0deg)

C0-180Plane IO= 2849cd

IES----





Intensity data: (deg , cd) CO-180

λ	I	λ	1	A	I	Α	1	A	I	λ	I
-90.0	0.4204	-58.5	5.318	-27.0	51.47	4.5	2074	36.0	19.93	67.5	2.477
-88.5	0.4460	-57.0	5.916	-25.5	62.18	6.0	1941	37.5	17.75	69.0	2.254
-87.0	0.5352	-55.5	6.508	-24.0	78.14	7.5	1765	39.0	15.92	70.5	2.014
-85.5	0.6503	-54.0	7.098	-22.5	105.0	9.0	1546	40.5	14.57	72.0	1.795
-84.0	0.7782	-52.5	7.758	-21.0	149.2	10.5	1302	42.0	13.47	73.5	1.603
-82.5	0.9064	-51.0	8.388	-19.5	218.8	12.0	1048	43.5	12.49	75.0	1.414
-81.0	1.033	-49.5	9.034	-18.0	317.4	13.5	805.7	45.0	11.59	76.5	1.278
-79.5	1.161	-48.0	9.653	-16.5	469.7	15.0	589.9	46.5	10.82	76.0	1.129
-78.0	1.276	-46.5	10.36	-15.0	663.7	16.5	411.2	48.0	10.09	79.5	0.9866
-76.5	1.442	-45.0	11.21	-13.5	8.888	18.0	271.9	49.5	9.328	81.0	0.8353
-75.0	1.607	-43.5	12.09	-12.0	1132	19.5	186.2	51.0	8.596	82.5	0.6948
-73.5	1.789	-42.0	13.15	-10.5	1376	21.0	131.4	52.5	7.856	84.0	0.5654
-72.0	1.994	-40.5	14.55	-9.0	1602	22.5	96.76	54.0	7.121	85.5	0.4280
-70.5	2.211	-39.0	16.24	-7.5	1802	24.0	74.81	55.5	6.393	87.0	0.3341
-69.0	2.429	-37.5	18.27	-6.0	1970	25.5	59.96	57.0	5.709	88.5	0.3312
-67.5	2.658	-36.0	20.66	-4.5	2101	27.0	49.37	58.5	5.023	90.0	0.3300
-66.0	2.915	-34.5	23.77	-3.0	2194	28.5	41.49	60.0	4.404		Ċ
-64.5	3.240	-33.0	27.57	-1.5	2244	30.0	35.35	61.5	3.832		m.
-63.0	3.691	-31.5	32.00	0.0	2249	31.5	30.39	63.0	3.337		
-61.5	4.201	-30.0	37.06	1.5	2223	33.0	26.03	64.5	2.978		
-60.0	4.750	-28.5	43.25	3.0	2168	34.5	22.63	66.0	2.720		

Electricity Parameter:

Current I: 0.1000A Power: 3.457W Voltage V: 34.59V PF: 1.000


Optical Parameter (Distance=2.559m):


Equivalent Luminous flux: Φ eff= 419.3lm Efficiency: Eff=121.30lm/W

CO-180Plane IO= 2249cd

D4







Intensity data: (deg , cd) C0-180

Α	I	A	1	λ	I	Α	1	Α	I	A	I
-90.0	0.2486	-58.5	6.487	-27.0	100.4	4.5	1142	36.0	20.77	67.5	2.382
-88.5	0.3282	-57.0	7.012	-25.5	143.6	6.0	1102	37.5	18.30	69.0	2.151
-87.0	0.4860	-55.5	7.556	-24.0	197.1	7.5	1043	39.0	16.20	70.5	1.920
-85.5	0.6111	-54.0	8.088	-22.5	263.3	9.0	968.7	40.5	14.62	72.0	1.687
-84.0	0.7587	-52.5	8.656	-21.0	341.9	10.5	879.1	42.0	13.39	73.5	1.492
-82.5	0.9060	-51.0	9.272	-19.5	428.5	12.0	775.6	43.5	12.40	75.0	1.329
-81.0	1.075	-49.5	9.984	-18.0	521.5	13.5	661.2	45.0	11.59	76.5	1.169
-79.5	1.267	-48.0	10.85	-16.5	619.8	15.0	541.1	46.5	10.89	78.0	1.033
-78.0	1.427	-46.5	11.91	-15.0	718.0	16.5	422.4	48.0	10.20	79.5	0.8898
-76.5	1.643	-45.0	13.19	-13.5	809.6	18.0	305.4	49.5	9.445	81.0	0.7554
-75.0	1.883	-43.5	14.74	-12.0	892.0	19.5	218.5	51.0	8.735	82.5	0.6501
-73.5	2.153	-42.0	16.72	-10.5	962.2	21.0	153.5	52.5	7.975	84.0	0.5551
-72.0	2.412	-40.5	19.13	-9.0	1019	22.5	108.7	54.0	7.271	85.5	0.5310
-70.5	2.700	-39.0	21.84	-7.5	1065	24.0	79.66	55.5	6.557	87.0	0.5536
-69.0	3.076	-37.5	24.75	-6.0	1100	25.5	60.76	57.0	5.886	88.5	0.5875
-67.5	3.521	-36.0	27.86	-4.5	1127	27.0	48.59	58.5	5.263	90.0	0.6101
-66.0	3.983	-34.5	31.47	-3.0	1148	28.5	40.36	60.0	4.668		
-64.5	4.449	-33.0	36.10	-1.5	1164	30.0	34.53	61.5	4.122		
-63.0	4.949	-31.5	42.83	0.0	1173	31.5	30.03	63.0	3.584		
-61.5	5.436	-30.0	53.44	1.5	1175	33.0	26.41	64.5	3.086		
-60.0	5.947	-28.5	71.28	3.0	1165	34.5	23.39	66.0	2.682		


Electricity Parameter:


Current I: 0.0A Power: 3.289W Voltage V: 32.90V PF: 1.000

Optical Parameter (Distance=2.410m):

CO-180Plane IO= 1173cd

IES----

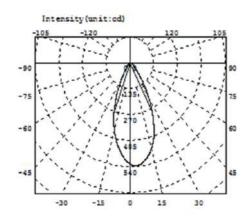



Intensity data: (deg , cd) C0-180

λ	1	λ	1	λ	1	λ	I	λ	1	λ	I
-90.0	2.777	-58.5	12.25	-27.0	156.9	4.5	531.6	36.0	110.0	67.5	10.34
-88.5	2.827	-57.0	13.16	-25.5	180.7	6.0	527.8	37.5	92.11	69.0	9.769
-87.0	2.979	-55.5	14.27	-24.0	205.5	7.5	520.9	39.0	77.29	70.5	9.237
-85.5	3.184	-54.0	15.50	-22.5	229.8	9.0	511.7	40.5	65.20	72.0	8.762
-84.0	3.503	-52.5	16.88	-21.0	255.1	10.5	500.6	42.0	55.46	73.5	8.281
-82.5	3.862	-51.0	18.43	-19.5	281.5	12.0	488.1	43.5	47.52	75.0	7.815
-81.0	4.260	-49.5	20.21	-18.0	306.5	13.5	473.6	45.0	41.19	76.5	7.333
-79.5	4.687	-48.0	22.23	-16.5	331.5	15.0	457.7	46.5	36.04	78.0	6.865
-78.0	5.164	-46.5	24.68	-15.0	354.9	16.5	438.9	48.0	31.83	79.5	6.323
-76.5	5.594	-45.0	27.46	-13.5	378.3	18.0	418.6	49.5	28.27	81.0	5.770
-75.0	6.235	-43.5	30.74	-12.0	400.1	19.5	396.1	51.0	25.29	82.5	5.237
-73.5	6.776	-42.0	34.56	-10.5	420.9	21.0	367.1	52.5	22.78	84.0	4.734
-72.0	7.270	-40.5	39.29	-9.0	440.0	22.5	341.0	54.0	20.62	85.5	4.266
-70.5	7.762	-39.0	44.80	-7.5	458.0	24.0	314.7	55.5	18.74	87.0	3.926
-69.0	8.257	-37.5	51.61	-6.0	474.6	25.5	287.5	57.0	17.13	88.5	3.238
-67.5	8.720	-36.0	59.87	-4.5	489.9	27.0	260.1	58.5	15.73	90.0	2.880
-66.0	9.166	-34.5	70.18	-3.0	503.5	28.5	232.7	60.0	14.51		
-64.5	9.663	-33.0	82.58	-1.5	514.9	30.0	205.4	61.5	13.40		
-63.0	10.21	-31.5	97.45	0.0	523.6	31.5	178.4	63.0	12.44		
-61.5	10.81	-30.0	114.8	1.5	529.5	33.0	153.3	64.5	11.66		
-60.0	11.49	-28.5	134.8	3.0	532.1	34.5	130.3	66.0	10.88		

Electricity Parameter:

Current I: 0.5000A Power: 17.29W Voltage V: 34.59V PF: 1.000

Optical Parameter (Distance=2.559m):

Equivalent Luminous flux: 4 eff= 395.61m Efficiency: Eff=22.871m/W

Diffuse angle: @(25%): 62.9deg@(50%): 47.0deg@(75%): 31.3deg@(50%): 47.0deg

Diffuse angle: @(25%): 63.1deg@(50%): 47.5deg@(75%): 32.1deg@(50%): 47.5deg

Imax=532.2cd (C=0.0deg,G=3.5deg)

C0-180Plane Imax= 532.2cd(G=3.5deg)

CO-180Plane IO= 523.6cd



			Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Jud gme nt	Remarks
	diamet	er	28			27. 79	27. 75	27.8	27. 73		
1.Size	thickne	ess	2			2. 07	2. 03	2. 07	2. 07		Test environment: In 20 °C -25 °C environment to
	thicknes	ss 2	0.8			0. 74	0. 76	0. 75	0. 76		achieve thermal equilibrium after the test.
	heigh	t	14.3			14. 29	14. 4	14. 39	14. 39		
							ne appearar				
				See	attachment	: "Appearan	ice Inspecti	on Standar	ds"		
2.Appear	ance		See ttachment ppearance E		1	No burr	No burr	No burr	No bu	rr	OK
Quality	Inspec Standa			_	N	o stains	No stains	No stains	No stai	ns	5.1
3.Material				PC	•		Color	Tra	nsparent		OK
4.Optica	to the so	recommended size and power rating of the source of the test, if it is required to be the actual conditions of the use environmental WHM				out of range nt, the lens	. According	to the heat fully tested	t dissipatio	n capa	ability of the lamp
	K-val					7. 66	7. 81	7. 35	7. 56	_	
	Efficie					83. 85%	83. 51%	87. 91%	86. 19%	_	
	Facula		the signatu	re sample		,	331313	311 3170	551 1575		
Compre judgi				•		l	Qı	ualified			
Remarks: 1. Tool Number: V-Vernier Caliper 2D-Quadratic H- Height Gauge M-Tool Microscope P-Needle T-				Length change (mm)	0.9 s 0.8 0.7 0.6 0.5	oduct size	changes v	vith tempe	Size	e: 50r e: 100	Omm Omm
Thick Gauge R-Radius Gauge E-Visual. 2 Ambient temperature on the size of the product refer to the table on the right					0.4 0.3 0.2 0.1 0	10	20 3	0 40	Size Size	e: 250	Omm
Precaulio	ms.								(℃)		

- Precautions:
- 1、Wear clean gloves during lens assembly to prevent contamination of the lens surface.
- 2. Take the lens try to avoid touching the total reflection surface.
- 3. When the lens surface contamination, you can only gently wipe with soft cotton sticky neat neutral solvent, not allowed to wipe with industrial solvents.
- 4. The working temperature of the lens should be within the temperature limit of the lens material. Exceeding the temperature limit will cause damage to the lens and affect the service life of the lens.



	S	tandard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Jud gme nt	Remarks
diamet	er	28			27. 85	27. 88	27. 9	27. 95		
thickne	ess	2			1. 96	1.94	1. 96	1. 93		Test environment: In 20 $^{\circ}$ C -25 $^{\circ}$ C environment to
thicknes	ss 2	8.0			0. 74	0. 73	0. 73	0.8		achieve thermal equilibrium after the test.
heigh	t	14.3			14. 2	14. 2	14. 2	14. 2		
			See	attachment	t "Appearan	ce Inspecti	on Standard	ds"		
ance	attacl	nment	F	1	No burr	No burr	No burr	No bu	rr	OK
	Inspe	ection	_	N	o stains	No stains	No stains	No stai	ns	
3.Material			PC			Color	Tra	nsparent		OK
The reco to the so and the a	he recommended size and power rating of the source of the test, if it is required to be				out of range ent, the lens See lig	source reco . According should be	to the heat fully tested ion curve	dissipatio and tested	n capa	ability of the lamp
	_								_	
	_									
		signatu	re sample		00.51%	00. 51%	00. 00%	00.00%		
hensive ment					J	Qı	ıalified			
Remarks: 1. Tool Number: V-Vernier Caliper 2D-Quadratic H- Height Gauge M-Tool Microscope P-Needle T- Thick Gauge R-Radius Gauge E-Visual. 2. Ambient temperature on the size of the product refer to the table on the right				0.9 0.8 0.7 0.6 0.5 0.4 0.3 0.2			*	Size: Size: Size: Size: Size: Size:	50mm 100m 150m 200m 250m	m m m
	thickness thickness thickness thickness theigh Testing L Testing L The reco to the so and the a FWHM angle K-val: Efficie Facula thensive ment Sumber: Valuadrara auge M-To pe P-Need uge R-Rad Visual. ent tempe of the prod	thickness thickness 2 height Testing LED The recommend to the source of and the actual of FWHM angle K-value Efficiency Facula See the hensive ment : Number: V-Vernie D-Quadratic Hauge M-Tool pe P-Needle T-uge R-Radius-Visual. ent temperature of the product reference of the product refe	thickness 2 See attachment "Appearance Inspection Standards" I Testing LED The recommended size atto the source of the test, and the actual conditions FWHM angle K-value Efficiency Facula See the signature thensive ment : Number: V-Vernier D-Quadratic H-auge M-Tool pe P-Needle T-uge R-Radius Visual. ent temperature on of the product refer	thickness 2 0.8 thickness 2 0.8 height 14.3 Gate See attachment "Appearance Inspection Standards" I PC Testing LED The recommended size and power reaction to the source of the test, if it is requand the actual conditions of the use FWHM angle K-value Efficiency Facula See the signature sample thensive ment : Number: V-Vernier D-Quadratic H-auge M-Tool pe P-Needle T-uge R-Radius Visual. ent temperature on of the product refer	thickness 2 0.8 thickness 2 0.8 height 14.3 Gate shear can See attachment See attachment "Appearance Inspection Standards" I PC Testing LED The recommended size and power rating of the to the source of the test, if it is required to be and the actual conditions of the use environment FWHM angle K-value Efficiency Facula See the signature sample thensive ment PC productions of the use environment PC productions of the use environment of the use	thickness 2 0.8 0.74 thickness 2 0.8 0.74 thickness 2 0.8 0.74 height 14.3 14.2 Gate shear can not affect the See attachment "Appearance Inspection Standards" No burr Testing LED The recommended size and power rating of the LED light to the source of the test, if it is required to be out of range and the actual conditions of the use environment, the lens FWHM See light angle 24.1° K-value 5.06 Efficiency 86.51% Facula See the signature sample hensive ment PC product size chemical size in the product reference on the right of the product reference o	diameter 28 27.85 27.88 thickness 2 0.8 0.74 0.73 height 14.3 14.2 14.2 Gate shear can not affect the appearar See attachment "Appearance Inspection Inspection Standards" PC Color Testing LED LED D4 The recommended size and power rating of the LED light source recot to the source of the test, if it is required to be out of range. According and the actual conditions of the use environment, the lens should be FWHM See light distribut angle 24.1° 23.6° K-value 5.06 5.21 Efficiency 86.51% 88.31% Facula See the signature sample hensive ment Quadratic Hauge M-Tool pe P-Needle T-uge R-Radius Visual. ent temperature on of the product refer le on the right	thickness 2 0.8 0.74 0.73 0.73 height 14.3 14.2 14.2 14.2 14.2 Gate shear can not affect the appearance of the late affact in standards and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested to the source of the test, if it is required to be out of range. According to the heat and the actual conditions of the use environment, the lens should be fully tested to the source of the standards and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment, the lens should be fully tested and the actual conditions of the use environment.	Size Size Imit result1 result2 result3 result4	diameter 28 Size limit size limit result1 result2 result3 result4 resu

Precautions:

- 1、Wear clean gloves during lens assembly to prevent contamination of the lens surface.
- 2. Take the lens try to avoid touching the total reflection surface.
- 3. When the lens surface contamination, you can only gently wipe with soft cotton sticky neat neutral solvent, not allowed to wipe with industrial solvents.
- 4. The working temperature of the lens should be within the temperature limit of the lens material. Exceeding the temperature limit will cause damage to the lens and affect the service life of the lens.



			Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Jud gme nt	Remarks
	diamet	er	28			27. 86	27.82	27. 85	27. 83		
1.Size	thickne	ess	2			2. 04	2. 03	2.01	2. 05		Test environment: In 20 °C -25 °C environment to
	thicknes	ss 2	0.8			0.8	0. 76	0.78	0.8		achieve thermal equilibrium after the test.
	heigh	t	14.3			14. 35	14. 37	14. 4	14. 4		
				Gate shear can not affect the appearance of the lamp See attachment "Appearance Inspection Standards"							
				See	attachment	t "Appearar	ice Inspecti	on Standar	ds"		
2.Appear	rance		See achment pearance E		1	No burr	No burr	No burr	No bu	rr	ОК
Quality	Inspec Standa		spection andards"		N	o stains	No stains	No stains	No stai	ns	
3.Materia	3.Material			PC			Color	Tra	nsparent		OK
	Testing I	LED					LED D4				
4.Optica	to the so	commended size and power rating of the LE source of the test, if it is required to be out of actual conditions of the use environment, to					. According	to the heat fully tested	t dissipatio	n capa	ability of the lamp
I index	angle	9				32. 3°	32.8°	31.3°	31.9°		
	K-val	ue				3. 04	2. 98	3. 21	3. 05		
	Efficie	ency				84.87%	84.90%	82. 79%	83. 31%		
	Facula	See	the signatu	re sample		,					
	ehensive ment		ı			•	Qι	ıalified			
	s: Number: \ 2D-Quadra			Lengtl chango (mm	h 0.9 es 0.8	roduct size	e changes v	with temp	→ Siz		
Microsco Thick Ga	auge M-Tope P-Needauge R-Ra	dle T-			0.5 0.4 0.3				Siz	ze: 20	00mm
2、Amb the size of	Sauge E-Visual. Ambient temperature on the size of the product refer to the table on the right				0.2	10	30	20 40	Siz		-
					0	10	20	30 40	(℃)		
Precaulio	ons:										

- Precautions:
- 1、Wear clean gloves during lens assembly to prevent contamination of the lens surface.
- 2. Take the lens try to avoid touching the total reflection surface.
- 3. When the lens surface contamination, you can only gently wipe with soft cotton sticky neat neutral solvent, not allowed to wipe with industrial solvents.
- 4. The working temperature of the lens should be within the temperature limit of the lens material. Exceeding the temperature limit will cause damage to the lens and affect the service life of the lens.



			Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Jud gme nt	Remarks
	diamet	er	28			27. 88	27. 9	27. 83	29. 93		
1.Size	thickne	ess	2			2. 09	2. 06	2. 11	2. 08		Test environment: In 20 ℃ -25 ℃ environment to
	thicknes	ss 2	0.8			0.86	0.86	0.83	0.85		achieve thermal equilibrium after the test.
	heigh	t	14.3			14. 36	14. 42	14. 37	14. 42		
							ne appearar		-		
				See	attachment	t "Appearan	ice Inspecti	on Standar	ds"	1	
2.Appear	ance		See achment pearance E —		1	No burr No bu		No burr	No bu	rr	OK
Quality	Inspection of the standard sta		spection andards"		N	o stains	No stains	No stains	No stai	ns	
3.Materia	3.Material			PC			Color	Tra	nsparent		ОК
	Testing I	_ED					LED D4				
	to the so	recommended size and power rating of the LED light source recommended for this lens should be compara the source of the test, if it is required to be out of range. According to the heat dissipation capability of the land the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens light distribution curve								ability of the lamp	
4.Optica I index							1		4.77	_	
l	angle						47. 1	47. 4	47	_	
	K-val				_						
	Efficie				_	79. 37%	77. 80%	77. 80%	77. 60%		
	Facula	See t	the signatu	re sample		Ì					
Compre judgi							Qı	ıalified			
				Lengtl	•	roduct size	e changes	with temp	erature t	table	
Caliper 2 Height Ga Microsco	Number: V D-Quadra auge M-To pe P-Neeo uge R-Rao	tic H- ool dle T-		•	es 0.8 0) 0.7 0.6 0.5 0.4 0.3			*	→ Siz → Siz → Siz → Siz → Siz	ze: 10 ze: 15 ze: 20	00mm 50mm 00mm
2、Ambi	Ambient temperature on the size of the product refer to the table on the right				0.2 0.1 0	10	20	30 40	→ Si:	ze: 30	00mm
Precautions:											

- Precautions:
- 1. Wear clean gloves during lens assembly to prevent contamination of the lens surface.
- 2. Take the lens try to avoid touching the total reflection surface.
- 3. When the lens surface contamination, you can only gently wipe with soft cotton sticky neat neutral solvent, not allowed to wipe with industrial solvents.
- 4. The working temperature of the lens should be within the temperature limit of the lens material. Exceeding the temperature limit will cause damage to the lens and affect the service life of the lens.



PI	V	HK-28@14-15-D4-21-	1g-1	Product Name	HK 28@14	-15°lens	i
Product	material	PC		Customer			
Package	diagram	Single Vac	cuum packa	ge Box	x package	?	>
Product	packing	33	A/ Box	4	pcs/Layer		
	. 0	17	Layer/Box	2244	A/ Carton		
	NO.	Part No	Part name	Size	Dosage	Unit	Remarks
	1	2.07.0026	Blister box	23cm*21cm	68	BAG	
Da alsa sin	2	2.08.0001	PE film	30cm*30cm	68	PCS	
Packagin g	3	2.06.0005	Reel label paper	6.2cm*8cm	68	PCS	
Materials	4	2.06.0005	Box label paper	6.2cm*9.2cm	1	PCS	
	5	2.06.0003	big plate	46.8cm*42.8cm	18	PCS	
	6	2.06.0015	big flat carton	48cm*44cm*19cn	n 1	PCS	
Remarks		The loose packing is not subjec	ct to this specif	ication. Customer's	requirements shall p	orevail	




Special notice


When gule pass through holes, columns and other structures, or part of the thin structure, will form a weld line. The product which uses multi-point injection welding line will appear because of the combination of sol, as shown below:


Syntneti





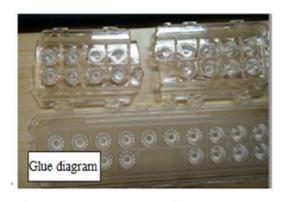

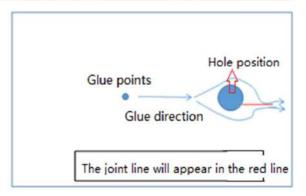

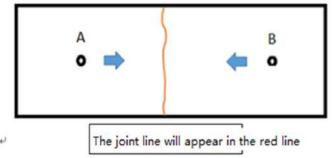

Please note:

The appearance of lines in the structure of the product as well as at the screw hole is a normal phenomenon, will not affect the actual use of the product, and can not be avoided at this stage.



Appearance inspection standards

1 Operating procedures

1.1.1Sampling standards, sampling plan and AQL

Test level : GB/T2828.1-2012The first part is according to the acceptance quality limit (AQL) retrieval batch inspection sampling plan, general inspection level Π level, CR class defect coefficient 0, MA defect rejection level AQL = 0.65, MI class defect rejection level AQL = 1.0; defect level please see 5.4.

2 Code table

Code	Code description	Unit	Code	Code description	Unit
N	Amount/pcs	pcs	D	Diameter	mm
L	Length	mm	Н	Depth	mm
W	Width	mm	DS	Distance	mm
S	Proportion	mm²	SS	Offset	mm

3 Test conditions

- 3.1 Sight distance and working hours: Sight distance should be 30-35cm, each side of the inspection time does not exceed 12s, the visual angle of 45-135 degrees;
- 3.2 Light: 2x40w cool white fluorescent lamp, the light source is 500-550mm away from the lens surface; in order to make the appearance defect can be correctly recognized, the illumination should be 500-1000Lux, and the observation time is 10 seconds.
 - 3.3 Visual inspection staff should be 1.0 (including corrected visual acuity) above, no color blindness, color weakness.

4 Appearance inspection standards

Test items	ludging standard	Inspection equipment	Defec	Defect level		
rescitents	Judging standard	Testing MI MA				
	When start the machine and process, all products have to check the appearance of the sample, the appearance of the sample is divided into qualified samples and limited samples.					
Check the sample	1: Qualified sample refers to the appearance and structure standard of the product which recognized by the client, the sample size should be confirmed before mass production;	Sample comparison , visual			√	

	_	Ī	ī	1
	2: The limited sample refers to the limit of a particular exceptionally developed sample. Limit the sample only for its specific point of exception to confirm; The priority is higher than the other criteria in this table. When there is a limited sample, the limit sample shall prevail.			
Raw edge	Not allowed to affect the size and assembly	Visual, point card	√	
Scratch	1: Non-optical surface and non-exposed surface scratches should be visually insignificant and the length is less than 1/10 of the maximum surface size.	Visual, point card, calipers	√	
Fingerprint	Fingerprints are not allowed on all products	Visual	√	
Foreign objects, black spots, white spots	The product may not be attached to foreign objects, including oil, fiber, dregs of water gap and so on			√
Deformation	Insufficient filling shall not affect the appearance of the assembly and the exposed surfaces.	Visual, feeler		√
Poor ejection	Products may not appear bad ejection, including no convex top, thimble printed on the assembly surface shall not be higher than the product surface, non-assembled surface thimble height should not exceed the product size tolerances; thimble printing should be less than the product surface and no more than 0.3; thimble surface treatment should be consistent with the product side. Ejection strain: the optical surface and the appearance of the exposed surface after assembly are not allowed to have a strain, and the structural surface does not allow visual obvious strain.	Visual, point card	√	
Insufficient filling	Insufficient filling shall not affect the appearance of the assembly and the exposed surfaces, The signature sample shall prevail.	Visual, point card	√	
Shrink	When the entire surface of the product shrinks, the optical properties and dimensions must meet the requirements, and the visual will not significantly affect the appearance.Part shrink reference point defects	Visual, point card	√	
Flow marks、Welding line	 1 : Product does not allow the presence of flow marks and welding lines unless the structure can not be avoided; 2: The remaining flow marks shall not appear in the optical surface, a single L ≤ 10mm, no more than two 	Visual	√	

Bubble	No bubbles are allowed	Visual		√	
Foreign objects, black spots, white spots	Not obvious or D ≤ 0.3mm black spots and foreign bodies in the area of 100x100mm not more than 1; Exceeded foreign matter black spots is judged bad.	Visual, point card	V		
Damaged	No damage is allowed	Visual			√
Cold glue	Optical surface may not have cold glue, non- optical surface cold glue should meet the visual is not obvious.	Visual	√		
	1: Do not affect the product size, shall not penetrate the optical surface, the cut should be smooth;				
Bad incision	2: Laser cutting products, the optical surface burns shall not occur after the processing is completed. Beading must not affect product installation	Visual			√
	3: Three molds and hot runner gate shall not appear residue.				
Scrub	Scrub surface should be uniform, off the scrub phenomenon should not be obvious , A single off scrub imprint requires D \leq 1 mm and no more than 1 area within a 50x50 mm area	Visual		√	