



HERCULUX
恒坤光电


Chengdu HercuLux Photoelectric
Technology Co.,Ltd
Product Approval

Approval number :

Customer :

Manufacturer : Chengdu HercuLux Photoelectric Technology Co.,Ltd

PN	Code	Product
HK-HG-62@30-15-D9-21-1g-1-JC	1. 01. 12852	HK Dark 62@30-15 degree lens(JC)
HK-HG-62@30-24-D9-21-1g-1-JC	1. 01. 12865	HK Dark 62@30-24 degree lens(JC)
HK-HG-62@30-36-D9-21-1g-1-JC	1. 01. 12993	HK Dark 62@30-36 degree lens(JC)
HK-HG-62@30-50-D9-21-1g-1-JC	1. 01. 12940	HK Dark 62@30-50 degree lens(JC)

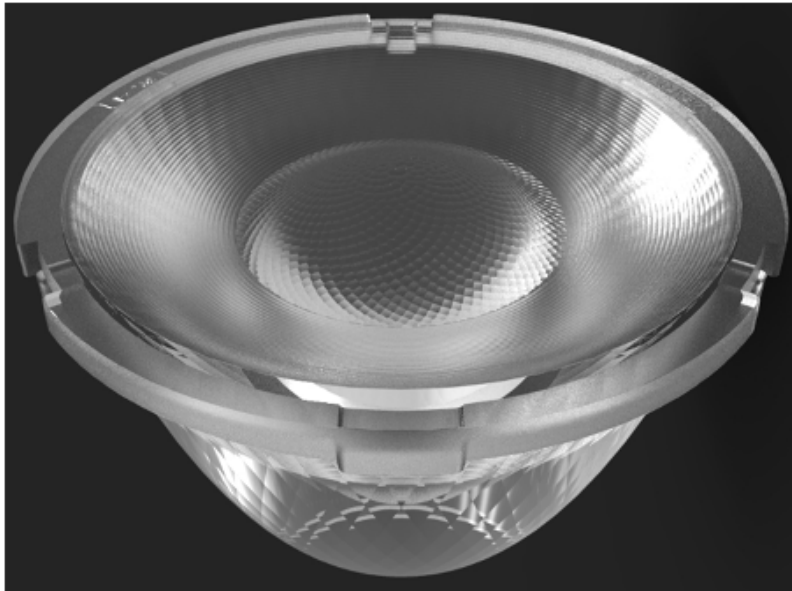

Supplier confirmation				Client confirmation			
Proposed		DATE		Qualified <input type="checkbox"/>		DATE	
Project manager		DATE		Unqualified <input type="checkbox"/>		DATE	
Audit		DATE		Audit		DATE	
Approved		DATE		Approved		DATE	
Stamp		DATE		Stamp		DATE	

(Confirmation of acceptance by both parties must be signed and sealed)

Factory: Chengdu Shuangliu District, Iot industrial park 2 road HercuLux Photoelectric Park

Phone : 028-85887727 (801) 028-85887990 (801)

Fax : 028-85887730

<http://www.herculux.cn/>

Sales Dept: Shenzhen Nanshan District Nanshan Cloud Valley Innovation Industrial Park Comprehensive Service Building, 501-505

TEL: 0755-2937 1541

FAX: 0755-2907 5140

*Approval In duplicate , for both supplier and customer.



HERCULUX
恒坤光电


Product Approval

TEL: 0755-2937 1541

FAX: 0755-2907 5140

<http://www.herculux.cn/>

Date updated: 2022/5/5

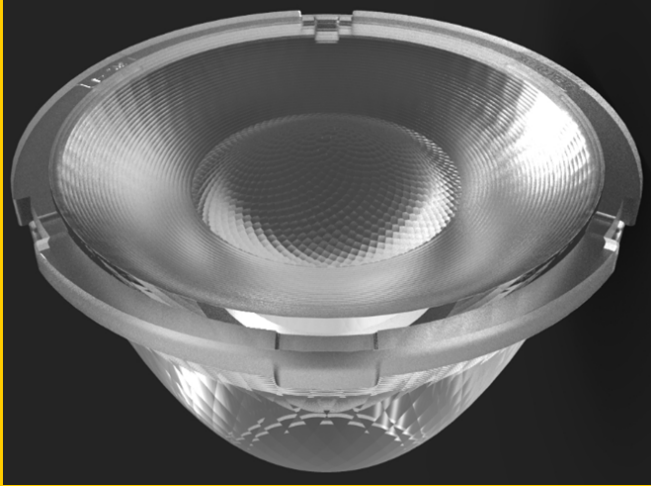
Product Picture:	
PN:	HK-HG-62@30-15-D9-21-1g-1-JC
Size(L*W*H/Φ*H):	Φ:62mm; H:30mm
Material:	PMMA
Efficiency:	\
Temperature(Topr):	Material limit temperature resistance: -40°C to +100°C Long-term use temperature: -40°C to +80°C
FWHM:	15°、24°、36°、50°
Matched LES:	D9

Technical remark:

1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.

Optical design			HK Dark 62@30-15 degree lens(JC)	HK-HG-62@30-15-D9-21-1g-1-JC		
Structure design					1.01.12852	
Review				Number of drawing	qty	weight
Validation				Material:	PMMA	CDHK

MT5 Tolerance table	Basic size	<3	3~10	10~24	24~65	65~140	140~250	250~450	>450
	tolerance value	±0.1	±0.15	±0.2	±0.35	±0.50	±0.80	±1.2	±2.0

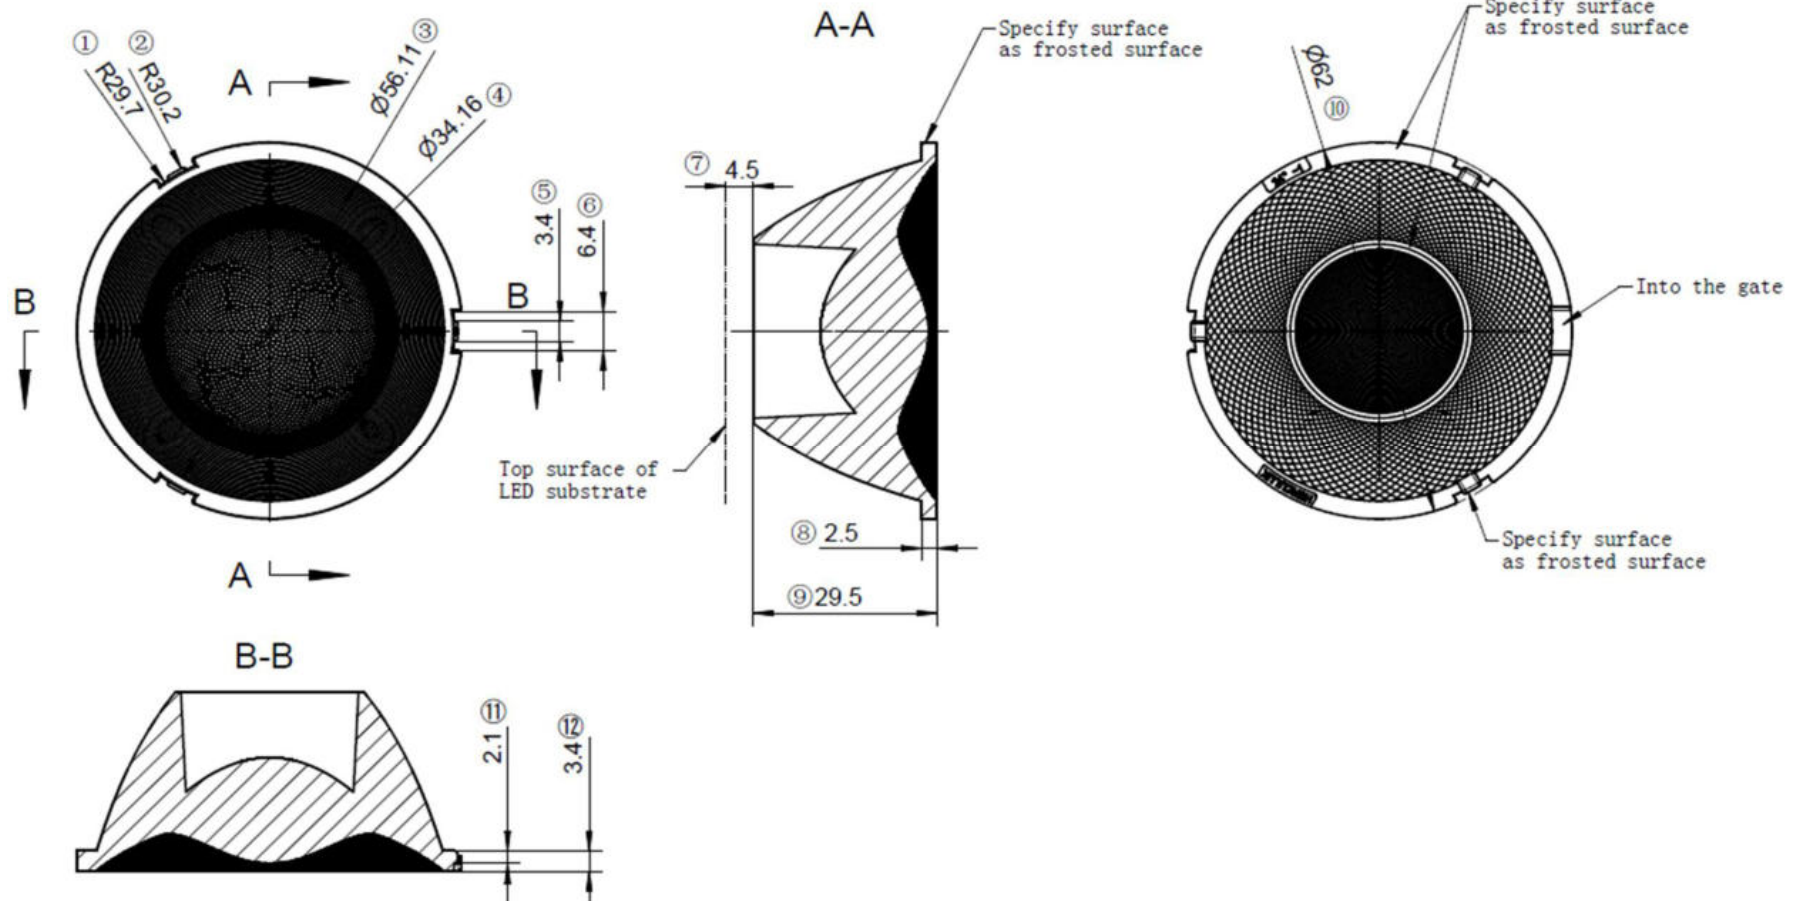

Technical remark:

1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.

Optical design			HK Dark 62@30-24 degree lens(JC)		HK-HG-62@30-24-D9-21-1g-1-JC		
Structure design					1.01.12865		
Review					Number of drawing	qty	weight
Validation			Material:	PMMA	CDHK		


MT5 Tolerance table	Basic size	<3	3~10	10~24	24~65	65~140	140~250	250~450	>450	
	tolerance val	±0.1	±0.15	±0.2	±0.35	±0.50	±0.80	±1.2	±2.0	

Technical remark:

1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.

Optical design			HK Dark 62@30-36 degree lens(JC)	HK-HG-62@30-36-D9-21-1g-1-JC		
Structure design					1.01.12993	
Review				Number of drawing	qty	weight
Validation				Material:	PMMA	CDHK

MT5 Tolerance table	Basic size	<3	3~10	10~24	24~65	65~140	140~250	250~450	>450	
	tolerance value	±0.1	±0.15	±0.2	±0.35	±0.50	±0.80	±1.2	±2.0	

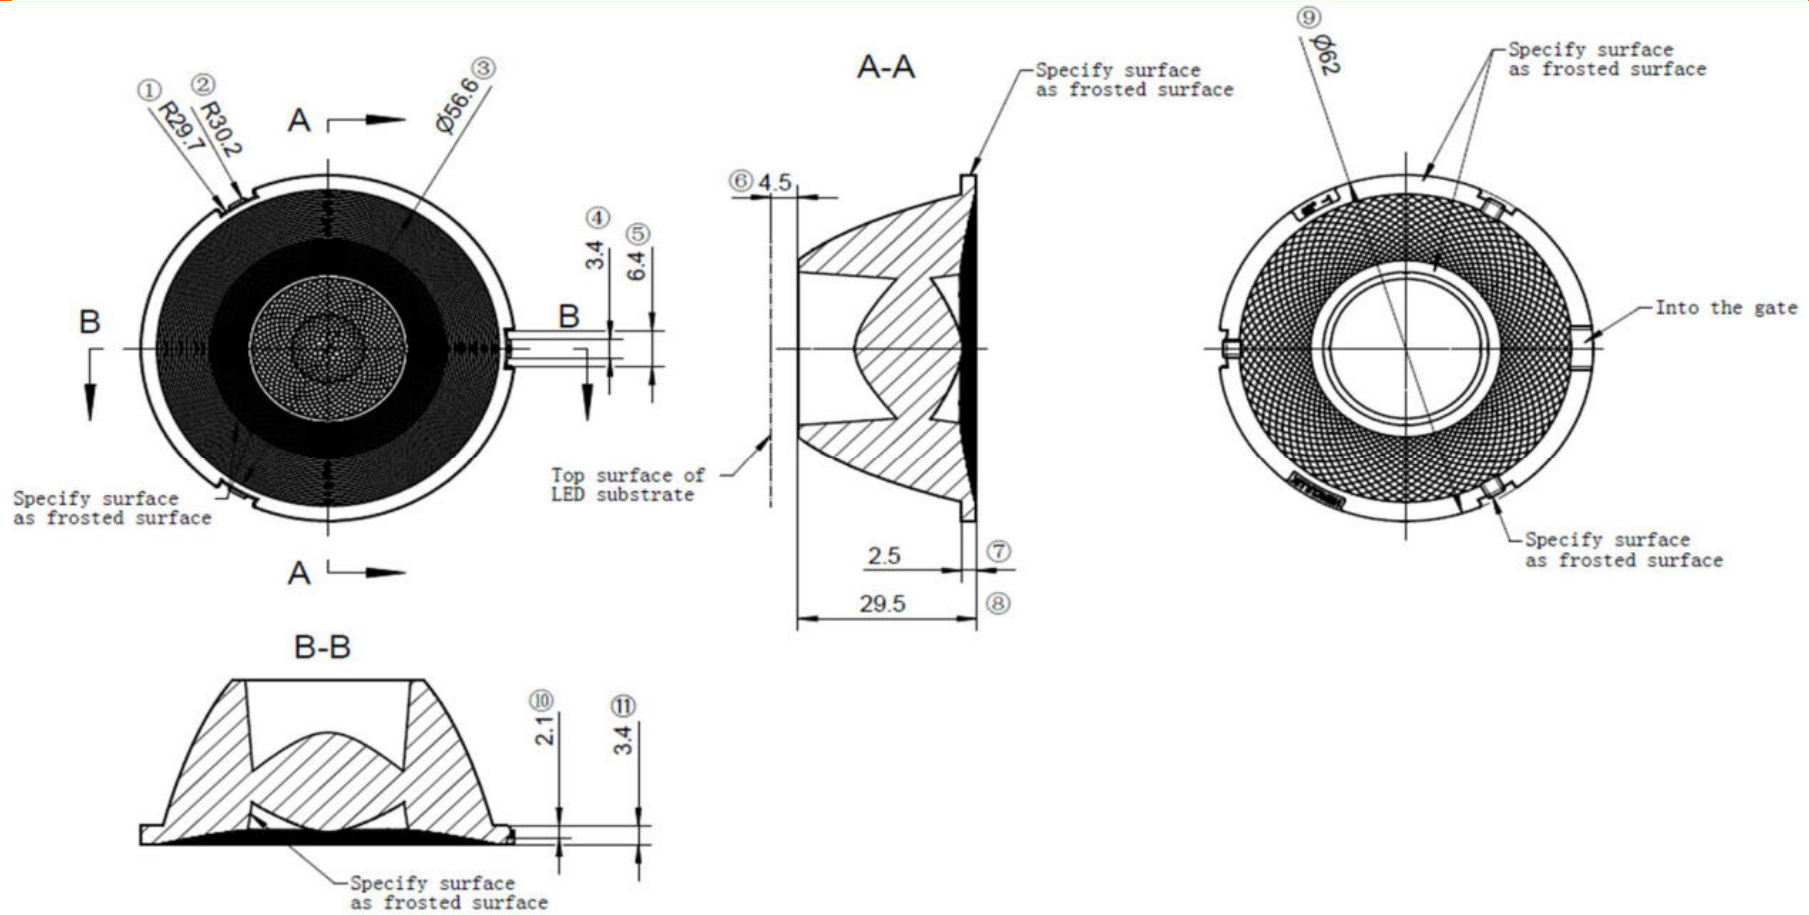

Technical remark:



1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.

Optical design			HK-HG-62@30-50-D9-21-1g-1-JC	
Structure design			HK Dark 62@30-50 degree lens(JC)	
Review			Number of drawing	1.01.12940
Validation			qty	weight
			Material:	PMMA
				CDHK

MT5 Tolerance table	Basic size	<3	3~10	10~24	24~65	65~140	140~250	250~450	>450
		tolerance val	± 0.1	± 0.15	± 0.2	± 0.35	± 0.50	± 0.80	± 1.2



GO1900L GONIOPHOTOMETER Test Report Page 1 Of 2

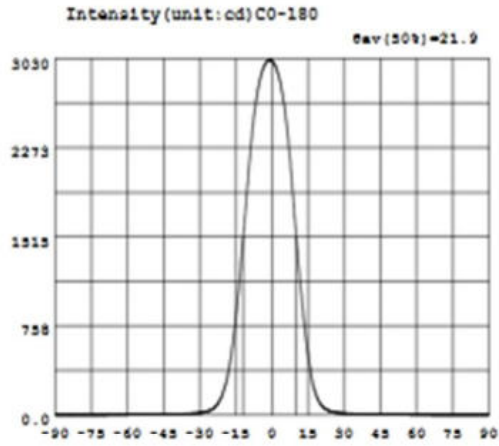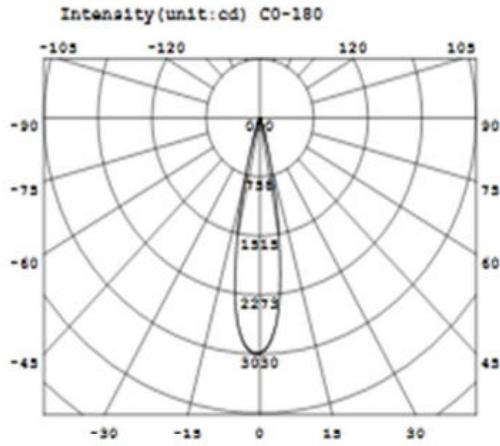

Intensity data:(deg , cd) C0-180

A	I	A	I	A	I	A	I	A	I	A	I
-90.0	0.4743	-58.5	5.461	-27.0	29.74	4.5	2706	36.0	6.601	67.5	2.200
-88.5	0.4523	-57.0	5.737	-25.5	41.45	6.0	2477	37.5	6.165	69.0	1.900
-87.0	0.5202	-55.5	5.911	-24.0	61.20	7.5	2160	39.0	5.826	70.5	1.644
-85.5	0.5885	-54.0	5.947	-22.5	96.93	9.0	1783	40.5	5.567	72.0	1.427
-84.0	0.6574	-52.5	5.895	-21.0	156.1	10.5	1402	42.0	5.404	73.5	1.237
-82.5	0.7370	-51.0	5.764	-19.5	246.3	12.0	1052	43.5	5.306	75.0	1.109
-81.0	0.8494	-49.5	5.603	-18.0	380.0	13.5	747.2	45.0	5.265	76.5	0.9924
-79.5	0.9390	-48.0	5.485	-16.5	581.0	15.0	502.0	46.5	5.349	78.0	0.8926
-78.0	1.074	-46.5	5.491	-15.0	844.9	16.5	308.3	48.0	5.489	79.5	0.7864
-76.5	1.198	-45.0	5.605	-13.5	1162	18.0	187.0	49.5	5.640	81.0	0.7070
-75.0	1.325	-43.5	5.797	-12.0	1510	19.5	112.7	51.0	5.766	82.5	0.6178
-73.5	1.542	-42.0	6.032	-10.5	1887	21.0	70.12	52.5	5.813	84.0	0.5495
-72.0	1.771	-40.5	6.188	-9.0	2252	22.5	46.73	54.0	5.725	85.5	0.4999
-70.5	2.081	-39.0	6.517	-7.5	2546	24.0	33.00	55.5	5.521	87.0	0.4645
-69.0	2.411	-37.5	7.121	-6.0	2755	25.5	24.06	57.0	5.204	88.5	0.4609
-67.5	2.862	-36.0	8.032	-4.5	2897	27.0	18.58	58.5	4.780	90.0	0.3875
-66.0	3.208	-34.5	9.332	-3.0	2981	28.5	14.82	60.0	4.344		
-64.5	3.656	-33.0	11.17	-1.5	3018	30.0	12.10	61.5	3.868		
-63.0	4.173	-31.5	13.57	0.0	3011	31.5	10.07	63.0	3.461		
-61.5	4.637	-30.0	17.03	1.5	2964	33.0	8.494	64.5	3.058		
-60.0	5.067	-28.5	22.11	3.0	2865	34.5	7.375	66.0	2.587		

Electricity Parameter:



Current I: 0.1000A Power: 3.358W
Voltage V: 33.59V PF: 1.000

Optical Parameter(Distance=2.410m):

Equivalent Luminous flux: $\Phi_{eff} = 466.8lm$ Efficiency: $Eff=139.02lm/W$
Diffuse angle: @ (25%): 28.8deg @ (50%): 21.9deg @ (75%): 15.9deg @ (50%): 21.9deg
Diffuse angle: @ (25%): 28.8deg @ (50%): 22.0deg @ (75%): 15.9deg @ (50%): 22.0deg
 $I_{max}=3020cd$ (C=0.0deg,G=-1.0deg) C0-180Plane $I_{max}= 3020cd$ (G=-1.0deg)
C0-180Plane $I_0= 3011cd$



GO1900L GONIOPHOTOMETER Test Report Page 1 Of 2

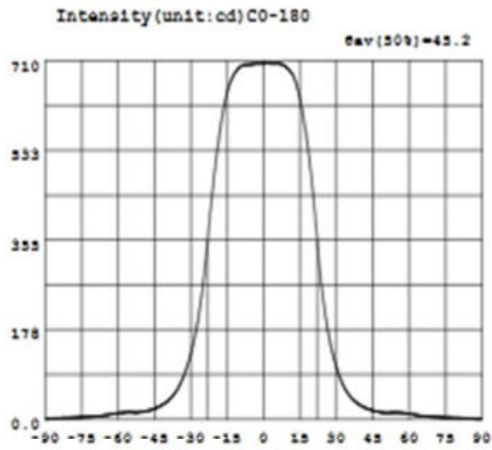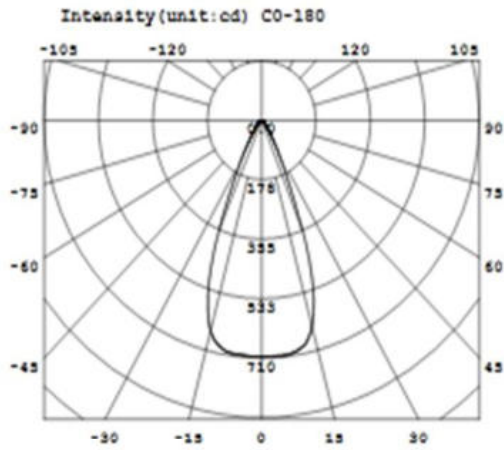

Intensity data:(deg , cd) C0-180


A	I	A	I	A	I	A	I	A	I	A	I
-90.0	1.129	-58.5	13.23	-27.0	197.6	4.5	704.6	36.0	43.76	67.5	5.776
-88.5	1.300	-57.0	13.84	-25.5	248.0	6.0	704.7	37.5	36.36	69.0	5.263
-87.0	1.606	-55.5	14.12	-24.0	311.3	7.5	703.3	39.0	30.70	70.5	4.746
-85.5	2.056	-54.0	13.95	-22.5	385.0	9.0	699.2	40.5	26.23	72.0	4.306
-84.0	2.217	-52.5	13.78	-21.0	456.6	10.5	692.7	42.0	22.65	73.5	3.933
-82.5	2.556	-51.0	14.19	-19.5	518.8	12.0	682.8	43.5	19.76	75.0	3.585
-81.0	2.787	-49.5	15.21	-18.0	571.3	13.5	663.6	45.0	17.44	76.5	3.268
-79.5	3.012	-48.0	16.70	-16.5	615.1	15.0	634.5	46.5	15.59	78.0	2.999
-78.0	3.430	-46.5	18.73	-15.0	648.0	16.5	595.4	48.0	14.14	79.5	2.695
-76.5	3.800	-45.0	21.11	-13.5	670.7	18.0	547.6	49.5	13.26	81.0	2.461
-75.0	4.205	-43.5	24.15	-12.0	684.8	19.5	488.0	51.0	12.97	82.5	2.177
-73.5	4.477	-42.0	27.94	-10.5	694.4	21.0	417.2	52.5	13.36	84.0	1.909
-72.0	4.901	-40.5	32.72	-9.0	700.5	22.5	330.8	54.0	13.69	85.5	1.519
-70.5	5.364	-39.0	38.66	-7.5	702.4	24.0	260.3	55.5	13.49	87.0	1.255
-69.0	5.903	-37.5	46.30	-6.0	702.7	25.5	204.9	57.0	12.87	88.5	1.011
-67.5	6.642	-36.0	56.09	-4.5	703.7	27.0	162.7	58.5	12.01	90.0	0.9659
-66.0	7.542	-34.5	68.96	-3.0	705.0	28.5	129.9	60.0	11.00		
-64.5	8.749	-33.0	85.17	-1.5	704.9	30.0	103.7	61.5	9.788		
-63.0	10.14	-31.5	105.4	0.0	704.9	31.5	82.50	63.0	8.506		
-61.5	11.32	-30.0	130.1	1.5	705.4	33.0	66.01	64.5	7.357		
-60.0	12.38	-28.5	161.1	3.0	704.8	34.5	53.34	66.0	6.482		


Electricity Parameter:


Current I: 0.1000A Power: 3.358W
Voltage V: 33.59V PF: 1.000


Optical Parameter (Distance=2.410m):


Equivalent Luminous flux: $\Phi_{eff} = 438.31lm$ Efficiency: $Eff=130.55lm/W$
Diffuse angle: @ (25%): 54.2deg @ (50%): 45.2deg @ (75%): 37.7deg @ (50%): 45.2deg
Diffuse angle: @ (25%): 54.2deg @ (50%): 45.2deg @ (75%): 37.7deg @ (50%): 45.2deg
 $I_{max}=705.4cd$ (C=0.0deg,G=1.5deg) C0-180Plane $I_{max}= 705.4cd$ (G=1.5deg)
C0-180Plane $I_0= 704.9cd$

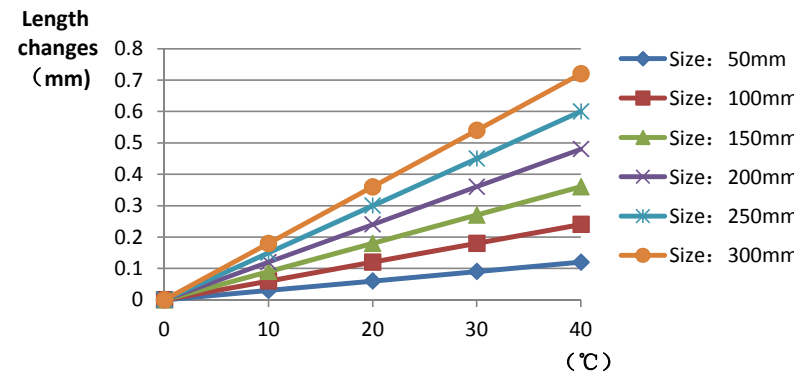		Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Judgment	Remarks																																									
1.Size	highly	29.5	/	/	/	/	/	/	/																																										
	The diameter of	62	/	/	/	/	/	/	/	Test environment: In 20 °C -25 °C environment to achieve thermal equilibrium after the test.																																									
	The thickness of the	2.5	/	/	/	/	/	/	/																																										
	Gate shear can not affect the appearance of the lamp																																																		
	See attachment "Appearance Inspection Standards"																																																		
2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr	OK																																												
			No stains	No stains	No stains	No stains																																													
3.Material	PMMA				Color	Transparent			OK																																										
4.Optical index	Testing LED	D9																																																	
	The recommended size and power rating of the LED light source recommended for this lens should be comparable to the source of the test, if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.																																																		
	FWHM	See light distribution curve																																																	
	K-value	/	/	/	/	/	/	/	/	/																																									
	angle	/	/	/	/	/	/	/	/	/																																									
	Efficiency	/	/	/	/	/	/	/	/	/																																									
Facula	See the signature sample																																																		
Comprehensive judgment	Qualified																																																		
Remarks:	<p>1、 Tool Number: V-Vernier Caliper 2D-Quadratic H-Height Gauge M-Tool Microscope P-Needle T-Thick Gauge R-Radius Gauge E-Visual.</p> <p>2、 Ambient temperature on the size of the product refer to the table on the right</p>																																																		
	<p style="text-align: center;">PMMA product size changes with temperature table</p>  <table border="1"> <caption>Data for PMMA product size changes with temperature table</caption> <thead> <tr> <th>Temperature (°C)</th> <th>50mm</th> <th>100mm</th> <th>150mm</th> <th>200mm</th> <th>250mm</th> <th>300mm</th> </tr> </thead> <tbody> <tr> <td>0</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> </tr> <tr> <td>10</td> <td>0.05</td> <td>0.08</td> <td>0.10</td> <td>0.12</td> <td>0.15</td> <td>0.18</td> </tr> <tr> <td>20</td> <td>0.10</td> <td>0.15</td> <td>0.20</td> <td>0.25</td> <td>0.30</td> <td>0.35</td> </tr> <tr> <td>30</td> <td>0.15</td> <td>0.22</td> <td>0.28</td> <td>0.35</td> <td>0.42</td> <td>0.50</td> </tr> <tr> <td>40</td> <td>0.20</td> <td>0.28</td> <td>0.35</td> <td>0.45</td> <td>0.55</td> <td>0.65</td> </tr> </tbody> </table>										Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm	0	0.00	0.00	0.00	0.00	0.00	0.00	10	0.05	0.08	0.10	0.12	0.15	0.18	20	0.10	0.15	0.20	0.25	0.30	0.35	30	0.15	0.22	0.28	0.35	0.42	0.50	40	0.20	0.28	0.35	0.45	0.55
Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm																																													
0	0.00	0.00	0.00	0.00	0.00	0.00																																													
10	0.05	0.08	0.10	0.12	0.15	0.18																																													
20	0.10	0.15	0.20	0.25	0.30	0.35																																													
30	0.15	0.22	0.28	0.35	0.42	0.50																																													
40	0.20	0.28	0.35	0.45	0.55	0.65																																													
<p>1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.</p> <p>2. Try to avoid touching the total reflection surface when taking the lens.</p> <p>3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).</p> <p>4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.</p>																																																			

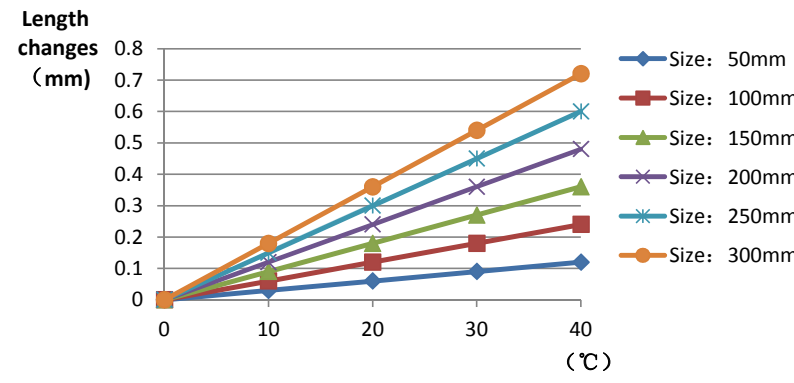	Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Judgment	Remarks																																									
1.Size	highly	29.5	/	29.43	29.44	29.49	19.44	/																																										
	The diameter of	62	/	61.68	61.74	61.73	61.74	/	Test environment: In 20 °C -25 °C environment to achieve thermal equilibrium after the test.																																									
	The thickness of the	2.5	/	2.58	2.54	2.5	2.53	/																																										
	Gate shear can not affect the appearance of the lamp																																																	
See attachment "Appearance Inspection Standards"																																																		
2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr	OK																																											
			No stains	No stains	No stains	No stains																																												
3.Material	PMMA			Color	Transparent		OK																																											
4.Optical index	Testing LED	D9																																																
	The recommended size and power rating of the LED light source recommended for this lens should be comparable to the source of the test, if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.																																																	
	FWHM	See light distribution curve																																																
	K-value	/	6.37	6.39	6.47	6.51	/																																											
	angle	/	22.4	22.1	21.9	21.8	/																																											
	Efficiency	/	91.00%	91.50%	91.40%	91.30%	/																																											
Facula	See the signature sample																																																	
Comprehensive judgment	Qualified																																																	
Remarks:	<p>1、 Tool Number: V-Vernier Caliper 2D-Quadratic H-Height Gauge M-Tool Microscope P-Needle T-Thick Gauge R-Radius Gauge E-Visual.</p> <p>2、 Ambient temperature on the size of the product refer to the table on the right</p>																																																	
	<p style="text-align: center;">PMMA product size changes with temperature table</p>  <table border="1"> <caption>Data for PMMA product size changes with temperature table</caption> <thead> <tr> <th>Temperature (°C)</th> <th>50mm</th> <th>100mm</th> <th>150mm</th> <th>200mm</th> <th>250mm</th> <th>300mm</th> </tr> </thead> <tbody> <tr> <td>0</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> </tr> <tr> <td>10</td> <td>0.05</td> <td>0.08</td> <td>0.10</td> <td>0.12</td> <td>0.15</td> <td>0.18</td> </tr> <tr> <td>20</td> <td>0.10</td> <td>0.15</td> <td>0.20</td> <td>0.25</td> <td>0.30</td> <td>0.35</td> </tr> <tr> <td>30</td> <td>0.15</td> <td>0.22</td> <td>0.28</td> <td>0.35</td> <td>0.42</td> <td>0.50</td> </tr> <tr> <td>40</td> <td>0.20</td> <td>0.28</td> <td>0.35</td> <td>0.45</td> <td>0.55</td> <td>0.65</td> </tr> </tbody> </table>									Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm	0	0.00	0.00	0.00	0.00	0.00	0.00	10	0.05	0.08	0.10	0.12	0.15	0.18	20	0.10	0.15	0.20	0.25	0.30	0.35	30	0.15	0.22	0.28	0.35	0.42	0.50	40	0.20	0.28	0.35	0.45	0.55
Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm																																												
0	0.00	0.00	0.00	0.00	0.00	0.00																																												
10	0.05	0.08	0.10	0.12	0.15	0.18																																												
20	0.10	0.15	0.20	0.25	0.30	0.35																																												
30	0.15	0.22	0.28	0.35	0.42	0.50																																												
40	0.20	0.28	0.35	0.45	0.55	0.65																																												
<p>1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.</p> <p>2. Try to avoid touching the total reflection surface when taking the lens.</p> <p>3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).</p> <p>4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.</p>																																																		

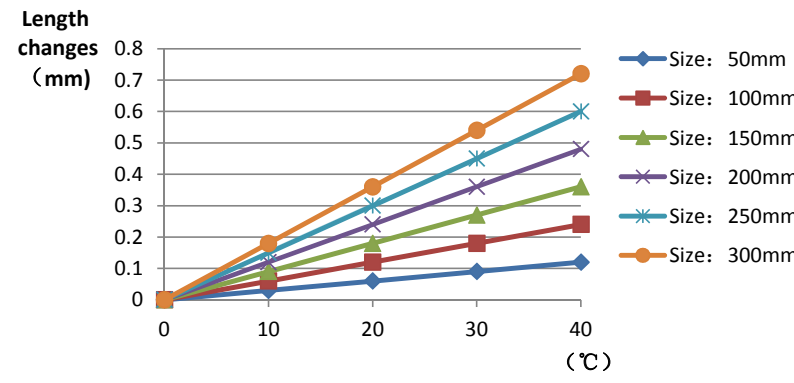		Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Judgment	Remarks																																									
1.Size	highly	29.5	/	/	/	/	/	/	/																																										
	The diameter of	62	/	/	/	/	/	/	/	Test environment: In 20 °C -25 °C environment to achieve thermal equilibrium after the test.																																									
	The thickness of the	2.5	/	/	/	/	/	/	/																																										
	Gate shear can not affect the appearance of the lamp																																																		
	See attachment "Appearance Inspection Standards"																																																		
2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr	OK																																												
			No stains	No stains	No stains	No stains																																													
3.Material	PMMA				Color	Transparent			OK																																										
4.Optical index	Testing LED	D9																																																	
	The recommended size and power rating of the LED light source recommended for this lens should be comparable to the source of the test, if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.																																																		
	FWHM	See light distribution curve																																																	
	K-value	/	/	/	/	/	/	/	/	/																																									
	angle	/	/	/	/	/	/	/	/	/																																									
	Efficiency	/	/	/	/	/	/	/	/	/																																									
Facula	See the signature sample																																																		
Comprehensive judgment	Qualified																																																		
Remarks:	<p>1、 Tool Number: V-Vernier Caliper 2D-Quadratic H-Height Gauge M-Tool Microscope P-Needle T-Thick Gauge R-Radius Gauge E-Visual.</p> <p>2、 Ambient temperature on the size of the product refer to the table on the right</p>																																																		
	<p style="text-align: center;">PMMA product size changes with temperature table</p>  <table border="1"> <caption>Data for PMMA product size changes with temperature table</caption> <thead> <tr> <th>Temperature (°C)</th> <th>50mm</th> <th>100mm</th> <th>150mm</th> <th>200mm</th> <th>250mm</th> <th>300mm</th> </tr> </thead> <tbody> <tr> <td>0</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> </tr> <tr> <td>10</td> <td>0.05</td> <td>0.08</td> <td>0.12</td> <td>0.15</td> <td>0.18</td> <td>0.22</td> </tr> <tr> <td>20</td> <td>0.10</td> <td>0.15</td> <td>0.22</td> <td>0.28</td> <td>0.35</td> <td>0.42</td> </tr> <tr> <td>30</td> <td>0.15</td> <td>0.22</td> <td>0.30</td> <td>0.38</td> <td>0.48</td> <td>0.58</td> </tr> <tr> <td>40</td> <td>0.20</td> <td>0.28</td> <td>0.38</td> <td>0.48</td> <td>0.60</td> <td>0.72</td> </tr> </tbody> </table>										Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm	0	0.00	0.00	0.00	0.00	0.00	0.00	10	0.05	0.08	0.12	0.15	0.18	0.22	20	0.10	0.15	0.22	0.28	0.35	0.42	30	0.15	0.22	0.30	0.38	0.48	0.58	40	0.20	0.28	0.38	0.48	0.60
Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm																																													
0	0.00	0.00	0.00	0.00	0.00	0.00																																													
10	0.05	0.08	0.12	0.15	0.18	0.22																																													
20	0.10	0.15	0.22	0.28	0.35	0.42																																													
30	0.15	0.22	0.30	0.38	0.48	0.58																																													
40	0.20	0.28	0.38	0.48	0.60	0.72																																													
<p>1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.</p> <p>2. Try to avoid touching the total reflection surface when taking the lens.</p> <p>3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).</p> <p>4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.</p>																																																			




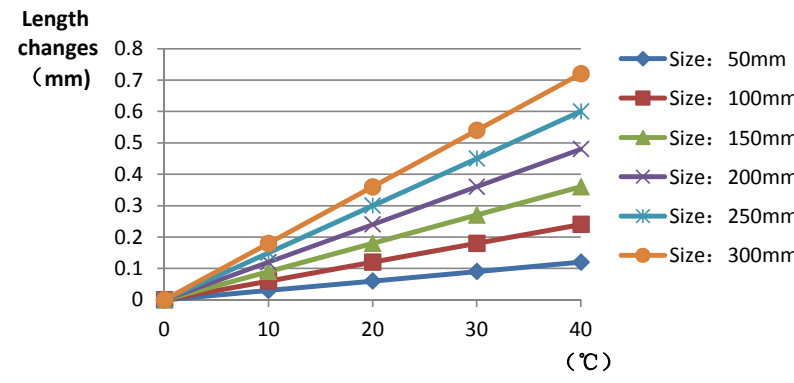
	Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Judgment	Remarks																																										
1.Size	highly	29.5	/	29.46	29.43	29.4	29.53	/	Test environment: In 20 °C -25 °C environment to achieve thermal equilibrium after the test.																																										
	The diameter of	62	/	61.79	62.1	62.03	62.13	/																																											
	The thickness of the	2.5	/	2.58	2.49	2.52	2.53	/																																											
	Gate shear can not affect the appearance of the lamp																																																		
See attachment "Appearance Inspection Standards"																																																			
2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr	OK																																												
			No stains	No stains	No stains	No stains																																													
3.Material	PMMA			Color	Transparent		OK																																												
4.Optical index	Testing LED	D9																																																	
	The recommended size and power rating of the LED light source recommended for this lens should be comparable to the source of the test, if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.																																																		
	FWHM	See light distribution curve																																																	
	K-value	/	1.61	1.61	1.64	1.59	/																																												
	angle	/	45.2	45.3	45	45.7	/																																												
	Efficiency	/	86.00%	86.00%	86.30%	86.60%	/																																												
Facula	See the signature sample																																																		
Comprehensive judgment	Qualified																																																		
Remarks:	<p>1、 Tool Number: V-Vernier Caliper 2D-Quadratic H-Height Gauge M-Tool Microscope P-Needle T-Thick Gauge R-Radius Gauge E-Visual.</p> <p>2、 Ambient temperature on the size of the product refer to the table on the right</p>																																																		
	<p style="text-align: center;">PMMA product size changes with temperature table</p>  <table border="1"> <caption>Data for PMMA product size changes with temperature table</caption> <thead> <tr> <th>Temperature (°C)</th> <th>50mm</th> <th>100mm</th> <th>150mm</th> <th>200mm</th> <th>250mm</th> <th>300mm</th> </tr> </thead> <tbody> <tr> <td>0</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> </tr> <tr> <td>10</td> <td>0.05</td> <td>0.08</td> <td>0.10</td> <td>0.12</td> <td>0.15</td> <td>0.18</td> </tr> <tr> <td>20</td> <td>0.10</td> <td>0.15</td> <td>0.20</td> <td>0.25</td> <td>0.30</td> <td>0.35</td> </tr> <tr> <td>30</td> <td>0.15</td> <td>0.22</td> <td>0.28</td> <td>0.35</td> <td>0.42</td> <td>0.50</td> </tr> <tr> <td>40</td> <td>0.20</td> <td>0.28</td> <td>0.35</td> <td>0.45</td> <td>0.55</td> <td>0.65</td> </tr> </tbody> </table>									Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm	0	0.00	0.00	0.00	0.00	0.00	0.00	10	0.05	0.08	0.10	0.12	0.15	0.18	20	0.10	0.15	0.20	0.25	0.30	0.35	30	0.15	0.22	0.28	0.35	0.42	0.50	40	0.20	0.28	0.35	0.45	0.55	0.65
Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm																																													
0	0.00	0.00	0.00	0.00	0.00	0.00																																													
10	0.05	0.08	0.10	0.12	0.15	0.18																																													
20	0.10	0.15	0.20	0.25	0.30	0.35																																													
30	0.15	0.22	0.28	0.35	0.42	0.50																																													
40	0.20	0.28	0.35	0.45	0.55	0.65																																													
<p>1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.</p> <p>2. Try to avoid touching the total reflection surface when taking the lens.</p> <p>3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).</p> <p>4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.</p>																																																			

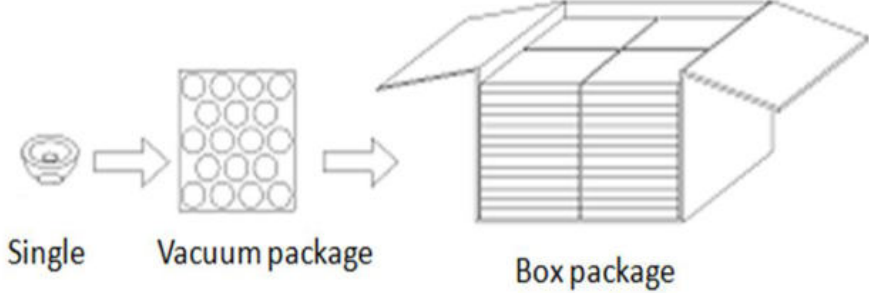PN	HK-HG-62@30-15-D9-21-1g-1-JC		Product Name	HK Dark 62@30-15 degree lens(JC)			
Product material	PMMA		Customer				
Package diagram	 <p style="text-align: center;"> Single Vacuum package Box package </p>						
Product packing	9	A/ Box	4	pcs/Layer			
	9	Layer/Box	324	A/ Carton			
Packaging Materials	NO.	Part No	Part name	Size	Dosage	Unit	Remarks
	1	2. 07. 0078	Blister box	23cm*21cm	36	BAG	
	2	2. 08. 0001	PE film	25cm*27cm	36	PCS	
	3	2. 06. 0005	Reel label paper	62mm*42mm	36	PCS	
	4	2. 06. 0005	Box label paper	62mm*70mm	1	PCS	
	5	2. 06. 0003	big plate	46cm*42cm	10	PCS	
	6	2. 06. 0011	big flat carton	48cm*44cm*37cm	1	PCS	
Remarks	Scattered packaging is not restricted by this specification, the customer has the requirements of the customer shall prevail						

Special notice

When glue pass through holes, columns and other structures, or part of the thin structure, will form a weld line. The product which uses multi-point injection welding line will appear because of the combination of sol, as shown below:

Synthesis

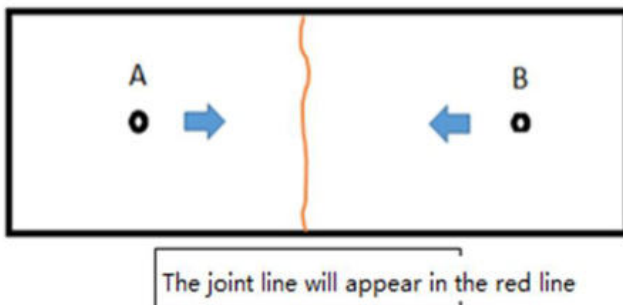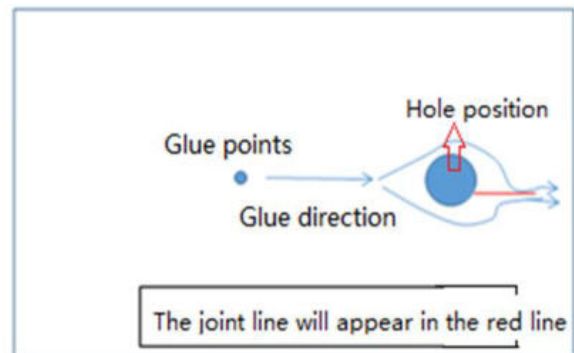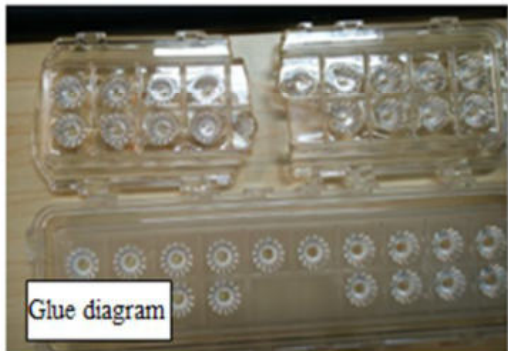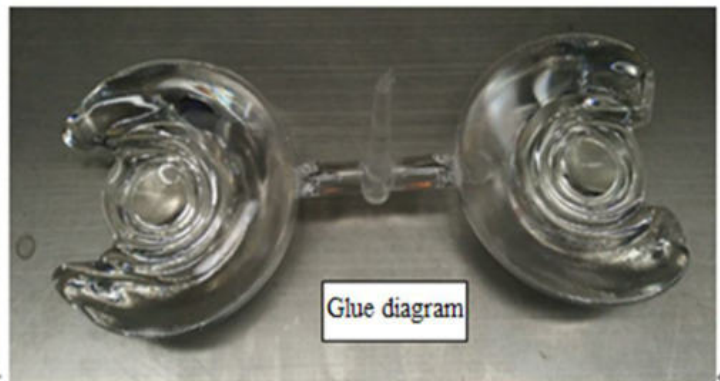

Please note :

The appearance of lines in the structure of the product as well as at the screw hole is a normal phenomenon, will not affect the actual use of the product, and can not be avoided at this stage.

Appearance inspection standards

1 Operating procedures

1.1.1 Sampling standards, sampling plan and AQL

Test level : GB/T2828.1-2012 The first part is according to the acceptance quality limit (AQL) retrieval batch inspection sampling plan, general inspection level II level, CR class defect coefficient 0, MA defect rejection level AQL = 0.65, MI class defect rejection level AQL = 1.0; defect level please see 5.4.

2 Code table

Code	Code description	Unit	Code		Code description	Unit
N	Amount/pcs	pcs	D		Diameter	mm
L	Length	mm	H		Depth	mm
W	Width	mm	DS		Distance	mm
S	Proportion	mm ²	SS		Offset	mm

3 Test conditions

3.1 Sight distance and working hours: Sight distance should be 30-35cm, each side of the inspection time does not exceed 12s, the visual angle of 45-135 degrees;

3.2 Light: 2x40w cool white fluorescent lamp, the light source is 500-550mm away from the lens surface; in order to make the appearance defect can be correctly recognized, the illumination should be 500-1000Lux, and the observation time is 10 seconds.

3.3 Visual inspection staff should be 1.0 (including corrected visual acuity) above, no color blindness, color weakness.

4 Appearance inspection standards

Test items	Judging standard	Inspection equipment	Defect level		
		Testing method	MI	MA	CR
Check the sample	When start the machine and process, all products have to check the appearance of the sample, the appearance of the sample is divided into qualified samples and limited samples.	Sample comparison , visual			
	1: Qualified sample refers to the appearance and structure standard of the product which recognized by the client, the sample size should be confirmed before mass production;				

	2: The limited sample refers to the limit of a particular exceptionally developed sample. Limit the sample only for its specific point of exception to confirm; The priority is higher than the other criteria in this table. When there is a limited sample, the limit sample shall prevail.				
Raw edge	Not allowed to affect the size and assembly	Visual, point card		√	
Scratch	1: Non-optical surface and non-exposed surface scratches should be visually insignificant and the length is less than 1/10 of the maximum surface size.	Visual, point card, calipers		√	
Fingerprint	Fingerprints are not allowed on all products	Visual		√	
Foreign objects, black spots, white spots	The product may not be attached to foreign objects, including oil, fiber, dregs of water gap and so on				√
Deformation	Insufficient filling shall not affect the appearance of the assembly and the exposed surfaces.	Visual, feeler			√
Poor ejection	Products may not appear bad ejection, including no convex top, thimble printed on the assembly surface shall not be higher than the product surface, non-assembled surface thimble height should not exceed the product size tolerances; thimble printing should be less than the product surface and no more than 0.3; thimble surface treatment should be consistent with the product side.	Visual, point card		√	
	Ejection strain: the optical surface and the appearance of the exposed surface after assembly are not allowed to have a strain, and the structural surface does not allow visual obvious strain.				
Insufficient filling	Insufficient filling shall not affect the appearance of the assembly and the exposed surfaces , The signature sample shall prevail.	Visual, point card		√	
Shrink	When the entire surface of the product shrinks, the optical properties and dimensions must meet the requirements, and the visual will not significantly affect the appearance.Part shrink reference point defects	Visual, point card		√	
Flow marks、Welding line	1 : Product does not allow the presence of flow marks and welding lines unless the structure can not be avoided;	Visual		√	
	2: The remaining flow marks shall not appear in the optical surface, a single $L \leq 10\text{mm}$, no more than two				

Bubble	No bubbles are allowed	Visual		√	
Foreign objects, black spots, white spots	Not obvious or $D \leq 0.3\text{mm}$ black spots and foreign bodies in the area of 100x100mm not more than 1; Exceeded foreign matter black spots is judged bad.	Visual, point card	√		
Damaged	No damage is allowed	Visual			√
Cold glue	Optical surface may not have cold glue, non-optical surface cold glue should meet the visual is not obvious.	Visual	√		
Bad incision	1: Do not affect the product size, shall not penetrate the optical surface, the cut should be smooth;	Visual			√
	2: Laser cutting products, the optical surface burns shall not occur after the processing is completed. Beading must not affect product installation				
	3: Three molds and hot runner gate shall not appear residue.				
Scrub	Scrub surface should be uniform, off the scrub phenomenon should not be obvious , A single off scrub imprint requires $D \leq 1\text{ mm}$ and no more than 1 area within a 50x50 mm area	Visual		√	



HERCULUX
恒坤光电


Chengdu HercuLux Photoelectric
Technology Co.,Ltd
Product Approval

Approval number :

Customer :

Manufacturer : Chengdu HercuLux Photoelectric Technology Co.,Ltd

PN	Code	Product
HK-HG-62@30-15-D9-21-1g-1	1. 01. 92023	HK Dark 62@30-15 degree lens
HK-HG-62@30-24-D9-21-1g-1	1. 01. 92040	HK Dark 62@30-24 degree lens
HK-HG-62@30-36-D9-21-1g-1	1. 01. 92072	HK Dark 62@30-36 degree lens
HK-HG-62@30-50-D9-21-1g-1	1. 01. 92180	HK Dark 62@30-50 degree lens

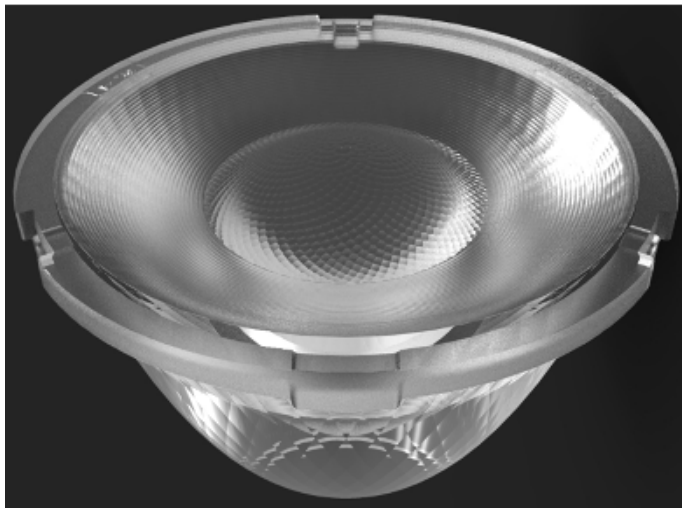

Supplier confirmation				Client confirmation			
Proposed		DATE		Qualified <input type="checkbox"/>		DATE	
Project manager		DATE		Unqualified <input type="checkbox"/>		DATE	
Audit		DATE		Audit		DATE	
Approved		DATE		Approved		DATE	
Stamp		DATE		Stamp		DATE	

(Confirmation of acceptance by both parties must be signed and sealed)

Factory: Chengdu Shuangliu District, Iot industrial park 2 road HercuLux Photoelectric Park

Phone : 028-85887727 (801) 028-85887990 (801)

Fax : 028-85887730

<http://www.herculux.cn/>

Sales Dept: Shenzhen Nanshan District Nanshan Cloud Valley Innovation Industrial Park Comprehensive Service Building, 501-

TEL: 0755-2937 1541

FAX: 0755-2907 5140

*Approval In duplicate , for both supplier and customer.

Disclaimer

Please use this product within the permitted range and environment according to the structure and material of the product. If the usage exceeds the recommended value, please test and verify by yourself. If the product is damaged due to out-of-range use, our company will not be responsible for the warranty.

Product material:

Customized products: The specifications and models of materials used are subject to the agreement between the two parties.

Conventional products: As a product that we continuously research and improve, under the premise of ensuring the quality and availability of the product, our company reserves the right to change the material. If the material specification and model change, without prior notice.

product data:

The measurement data and dimensional tolerances of the 2D drawings in the product data sheet of this acknowledgement are for reference only, and the final size shall prevail in kind.

The measurement data presented in this acknowledgment is a performance test of the product based on our company's internal test conditions and quality requirements, and the reported data is a typical value of the average results of multiple measurements. Therefore, in some cases, the actual product may deviate from the data provided. We reserve the right to notify you in advance of this data.

Product changes and improvements:

Changes and improvements of customized products are subject to the agreement between the two parties in the contract or technical documents.

As the conventional products that we continue to research and improve, our company reserves the right to make technical changes to its products, and reserves the right to make changes to data resulting from improvements without prior notice.

Operation cautions:

1. Please wear clean gloves during product assembly to prevent product surface contamination.
2. Try to avoid touching the optical surface of the lens when taking the lens.
3. When the surface of the product is polluted, please wipe it gently with a soft cotton cloth dipped in analytically pure neutral solvent. It is forbidden to use industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA monomer, etc.) wipe.
4. The lens made of PC should not be exposed to direct sunlight in the storage and use environment. If the lens turns yellow or cracks due to long-term sunlight exposure, our company will not be responsible for the warranty.



HERCULUX
恒坤光电


Basic product information


TEL: 0755-2937 1541

FAX: 0755-2907 5140

<http://www.herculux.cn/>

Date updated: 2023/5/17

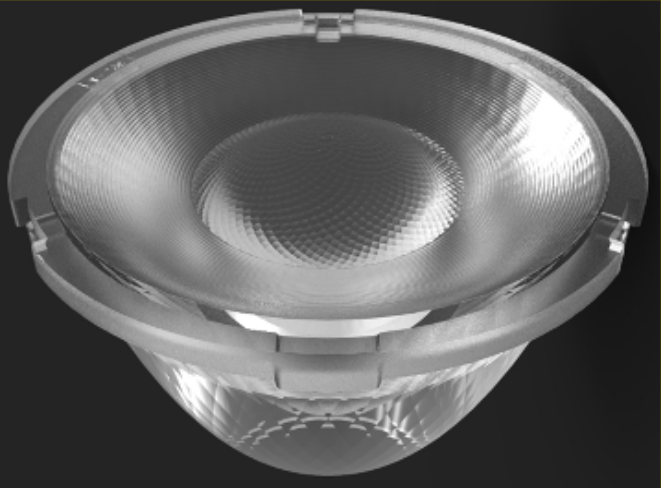Product Picture:	
Size(L*W*H/Φ*H):	Φ:62mm; H:30mm
Material:	PMMA
Efficiency:	\
Temperature(Topr):	Material extreme temperature resistance : -40°C to +100°C long-term use temperature : -40°C to +80°C
FWHM:	15°、24°、36°、50°
Matched LES:	D9
Recommended MAX power:	30W

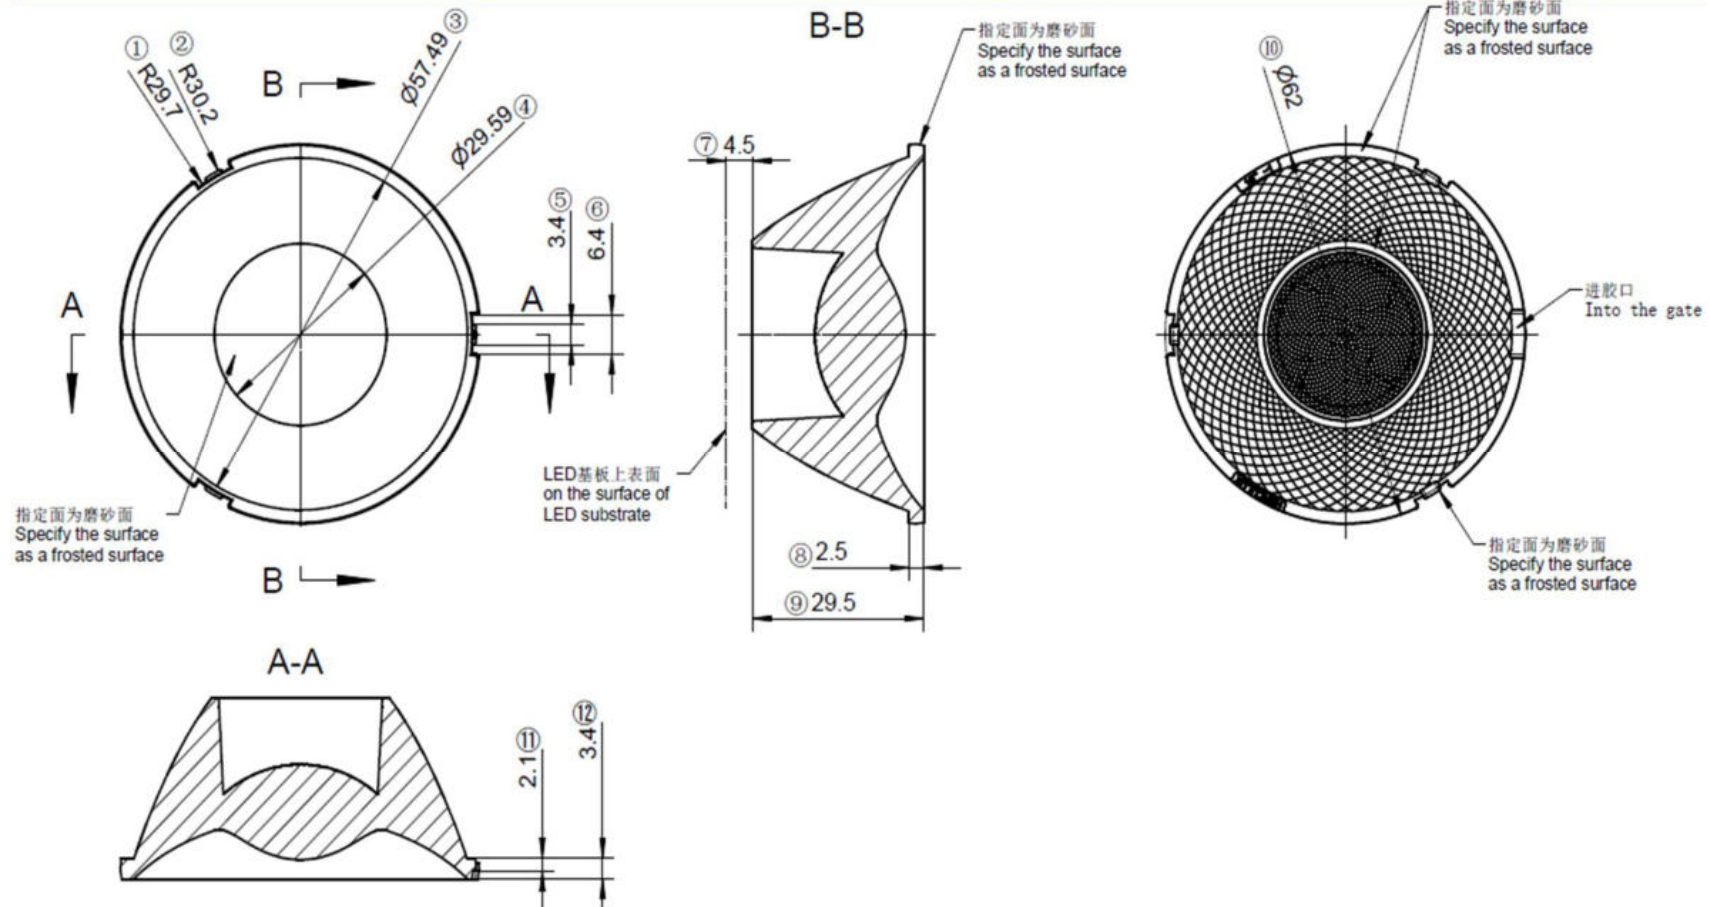


Technical remark:

1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.
- *4. When the lamp adopts rubber ring for waterproofing: the roughness of the contact surface between the radiator and the rubber ring is required: $Ra < 3.2\mu m$

Optical design			HK Dark 62@30-15 degree lens		HK-HG-62@30-15-D9-21-1g-1		
Structure design					1.01.92023		
Review					number of draw	qty	weight
Validation			Material: PMMA		CDHK		

MT5 Tolerance table	Basic size	<3	3~10	10~24	24~65	65~140	140~250	250~450	>450
	olerance val	±0.1	±0.15	±0.2	±0.35	±0.50	±0.80	±1.2	±2.0

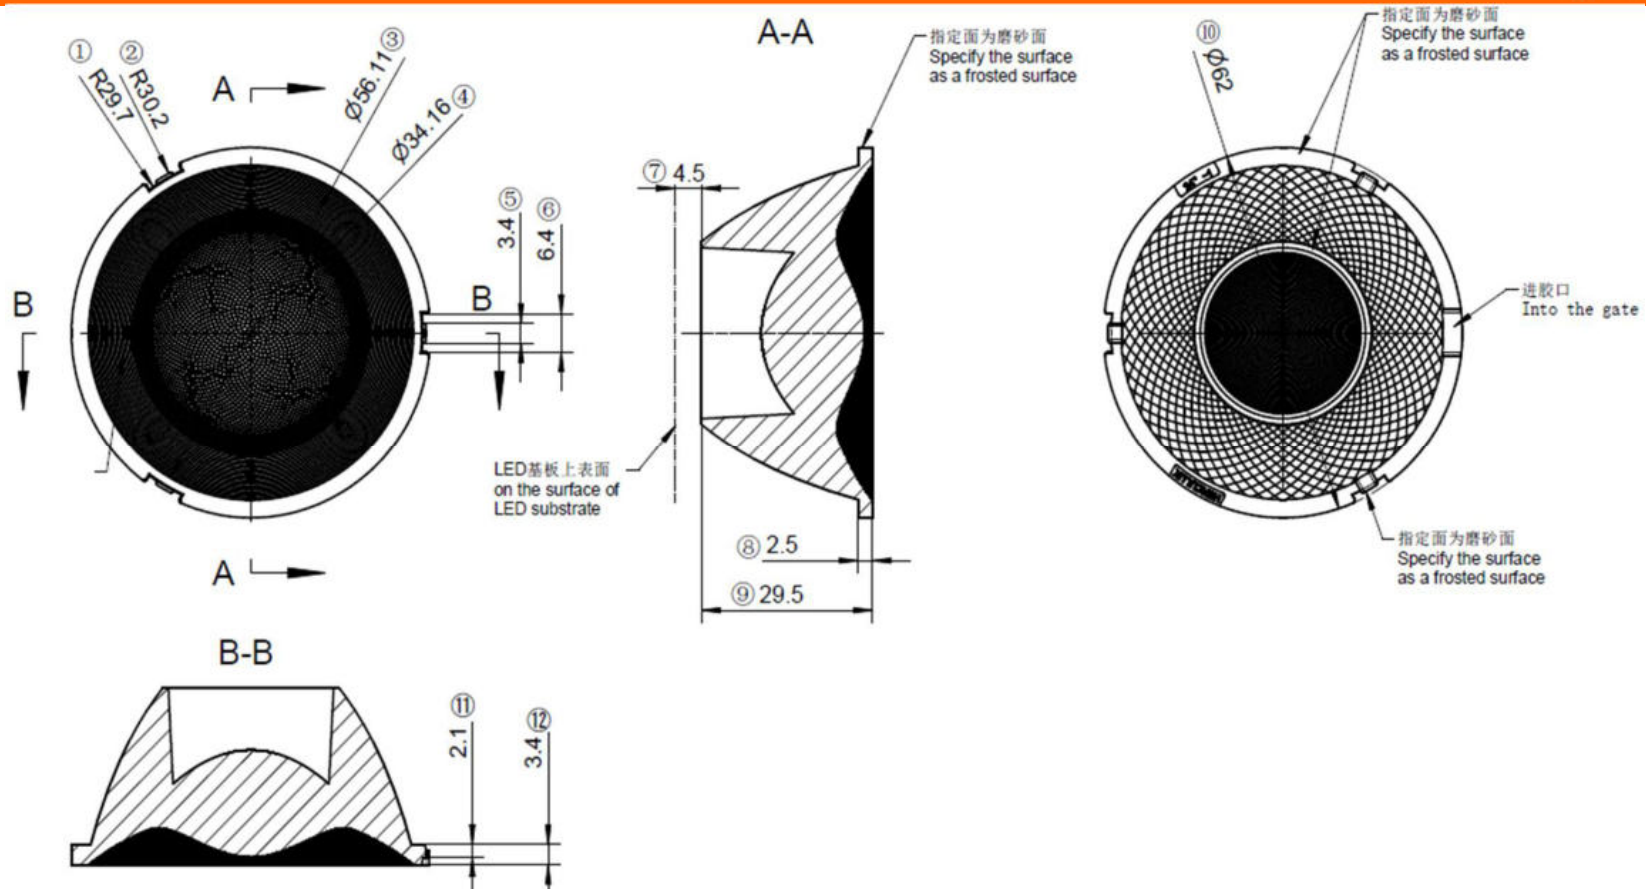


Technical remark:

1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.
- *4. When the lamp adopts rubber ring for waterproofing: the roughness of the contact surface between the radiator and the rubber ring is required: $Ra < 3.2\mu m$

Optical design			HK Dark 62@30-24 degree lens		HK-HG-62@30-24-D9-21-1g-1		
Structure design					1.01.92040		
Review					number of draw	qty	weight
Validation			Material:	PMMA	CDHK		

MT5 Tolerance table	Basic size	<3	3~10	10~24	24~65	65~140	140~250	250~450	>450
	olerance val	±0.1	±0.15	±0.2	±0.35	±0.50	±0.80	±1.2	±2.0

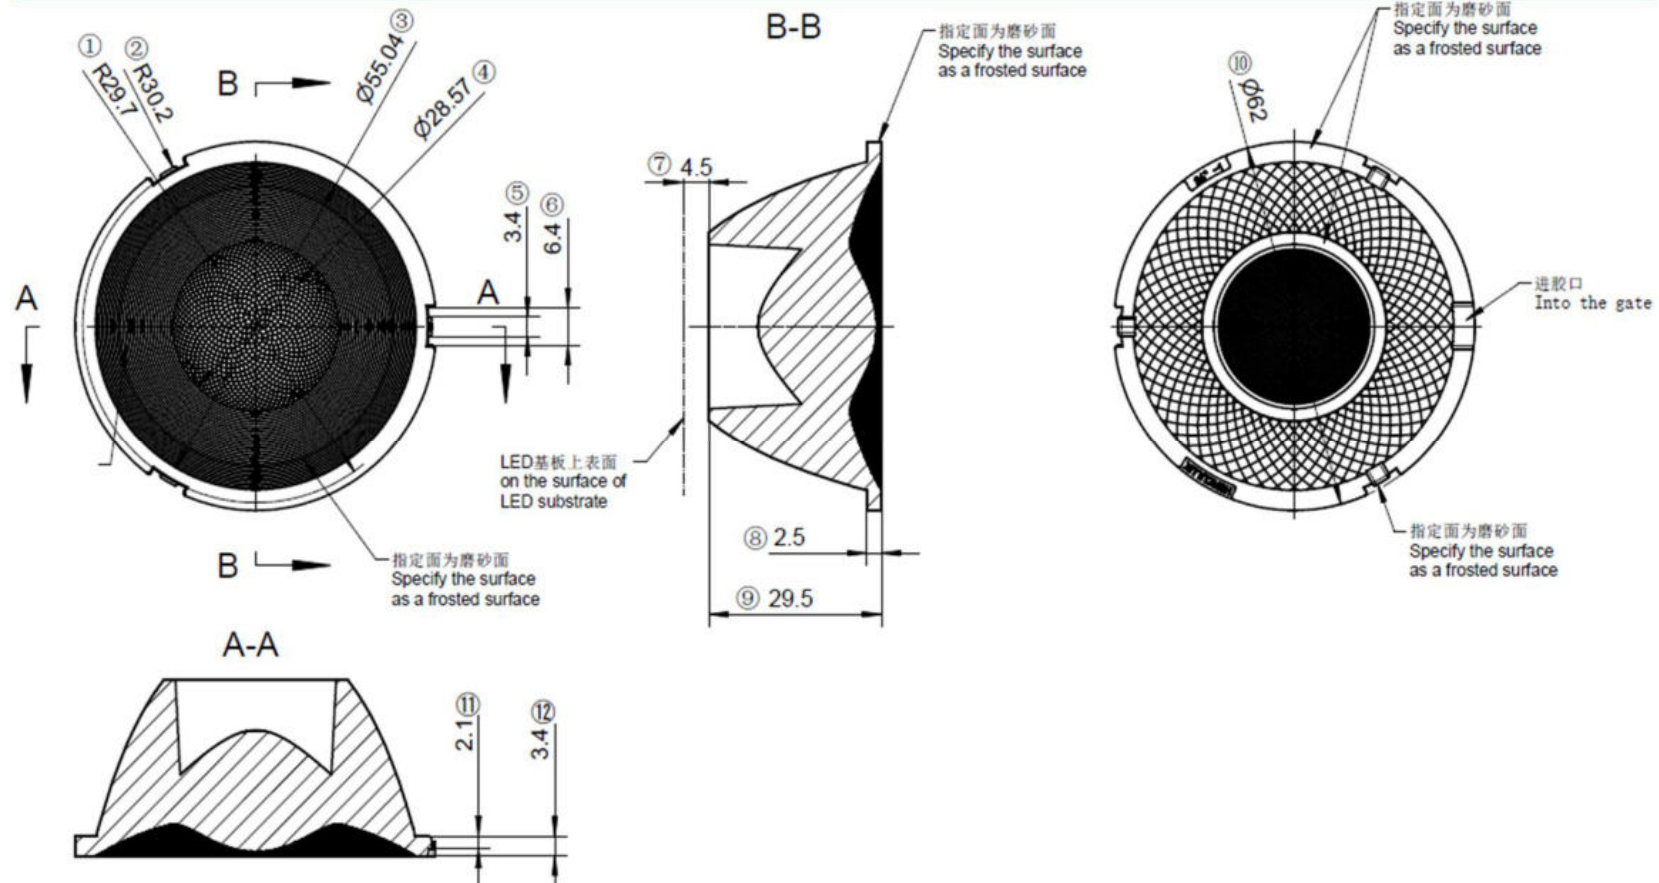


Technical remark:

1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.
- *4. When the lamp adopts rubber ring for waterproofing: the roughness of the contact surface between the radiator and the rubber ring is required: $Ra < 3.2\mu m$

Optical design			HK Dark 62@30-36 degree lens	HK-HG-62@30-36-D9-21-1g-1		
Structure design				1.01.92072		
Review				number of draw	qty	weight
Validation			Material:	PMMA	CDHK	

MT5 Tolerance table	Basic size	<3	3~10	10~24	24~65	65~140	140~250	250~450	>450
	olerance val	±0.1	±0.15	±0.2	±0.35	±0.50	±0.80	±1.2	±2.0


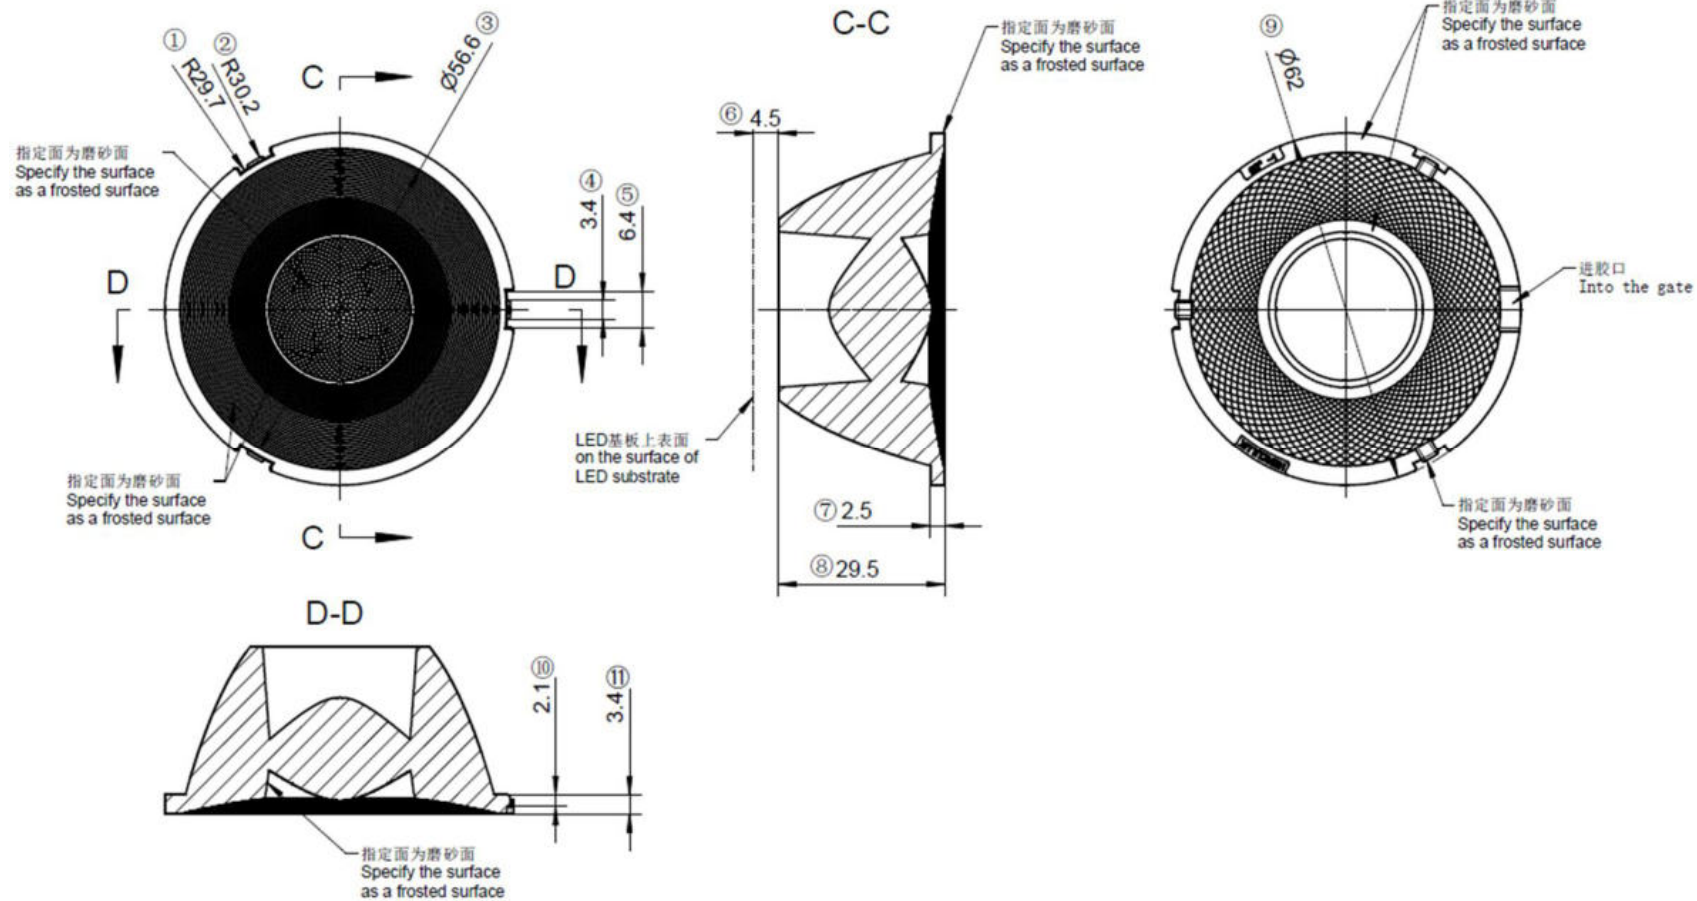


Technical remark:

1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.
- *4. When the lamp adopts rubber ring for waterproofing: the roughness of the contact surface between the radiator and the rubber ring is required: Ra<3.2µm

Optical design			HK Dark 62@30-50 degree lens		HK-HG-62@30-50-D9-21-1g-1		
Structure design					1.01.92180		
Review					number of draw	qty	weight
Validation			Material: PMMA		CDHK		

MT5 Tolerance table	Basic size	<3	3~10	10~24	24~65	65~140	140~250	250~450	>450
	olerance val	±0.1	±0.15	±0.2	±0.35	±0.50	±0.80	±1.2	±2.0

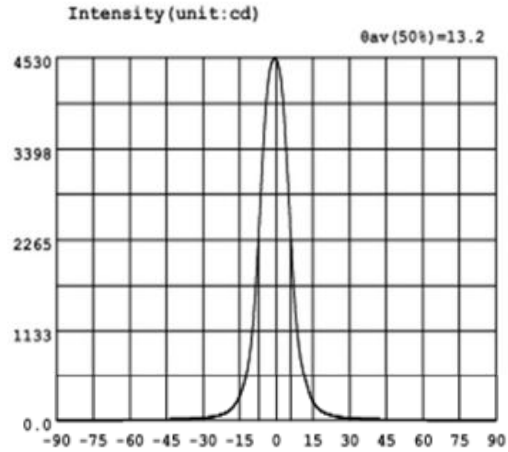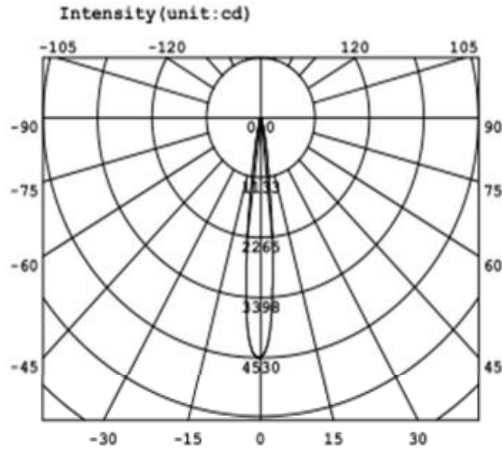

Intensity data:(deg , cd) C0-180

A	I	A	I	A	I	A	I	A	I	A	I
-90.0	1.028	-58.5	9.451	-27.0	43.90	4.5	3169	36.0	21.51	67.5	5.711
-88.5	1.050	-57.0	10.01	-25.5	51.32	6.0	2309	37.5	20.11	69.0	5.238
-87.0	1.142	-55.5	10.56	-24.0	60.46	7.5	1537	39.0	18.62	70.5	4.776
-85.5	1.312	-54.0	11.12	-22.5	73.42	9.0	1021	40.5	17.21	72.0	4.361
-84.0	1.516	-52.5	11.71	-21.0	91.59	10.5	705.6	42.0	15.96	73.5	3.872
-82.5	1.766	-51.0	12.27	-19.5	118.7	12.0	503.3	43.5	14.87	75.0	3.428
-81.0	2.117	-49.5	12.81	-18.0	159.3	13.5	346.1	45.0	14.21	76.5	2.982
-79.5	2.516	-48.0	13.38	-16.5	221.1	15.0	238.2	46.5	13.57	78.0	2.580
-78.0	2.935	-46.5	14.01	-15.0	311.5	16.5	170.6	48.0	13.04	79.5	2.207
-76.5	3.399	-45.0	14.72	-13.5	435.6	18.0	127.8	49.5	12.49	81.0	1.812
-75.0	3.854	-43.5	15.65	-12.0	615.2	19.5	99.63	51.0	11.96	82.5	1.542
-73.5	4.296	-42.0	16.78	-10.5	910.3	21.0	80.28	52.5	11.40	84.0	1.320
-72.0	4.746	-40.5	18.06	-9.0	1408	22.5	65.91	54.0	10.84	85.5	1.145
-70.5	5.179	-39.0	19.46	-7.5	2152	24.0	55.14	55.5	10.25	87.0	1.009
-69.0	5.643	-37.5	20.97	-6.0	3015	25.5	46.30	57.0	9.631	88.5	0.9842
-67.5	6.131	-36.0	22.39	-4.5	3802	27.0	39.59	58.5	9.031	90.0	1.037
-66.0	6.663	-34.5	24.09	-3.0	4296	28.5	34.56	60.0	8.465		
-64.5	7.208	-33.0	26.62	-1.5	4496	30.0	30.55	61.5	7.884		
-63.0	7.783	-31.5	29.69	0.0	4513	31.5	27.32	63.0	7.312		
-61.5	8.339	-30.0	33.27	1.5	4357	33.0	24.94	64.5	6.732		
-60.0	8.906	-28.5	37.90	3.0	3924	34.5	23.07	66.0	6.197		



Electricity Parameter:

Current I: 0.1000A Power: 3.500W
Voltage V: 35.00V PF: 1.000

Optical Parameter(Distance=2.410m):

Equivalent Luminous flux: $\Phi_{eff} = 382.21m$ Efficiency: $Eff=109.23lm/W$
Diffuse angle: @ (25%): 18.3deg@ (50%): 13.2deg@ (75%): 9.3deg @ (50%): 13.2deg
Diffuse angle: @ (25%): 18.3deg@ (50%): 13.3deg@ (75%): 9.3deg @ (50%): 13.3deg
 $I_{max}=4524cd$ (C=0.0deg,G=-0.5deg) C0-180Plane $I_{max}= 4524cd$ (G=-0.5deg)
C0-180Plane $I_{0}= 4513cd$

GO1900L GONIOPHOTOMETER Test Report Page 1 Of 2

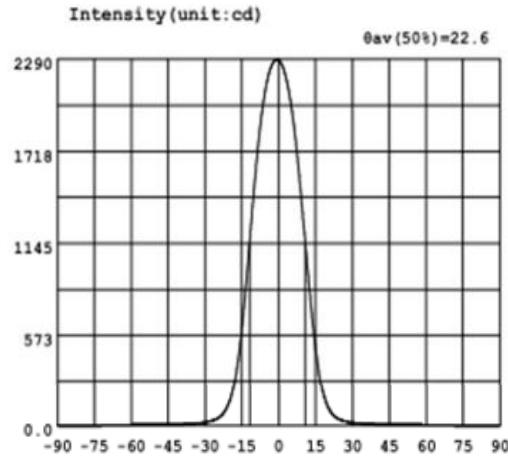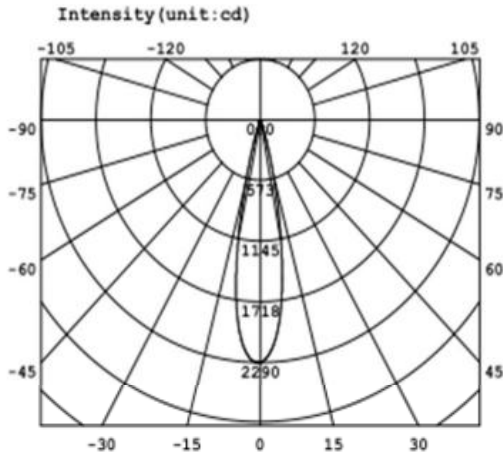

Intensity data:(deg , cd) C0-180

A	I	A	I	A	I	A	I	A	I	A	I
-90.0	0.9265	-58.5	8.212	-27.0	33.48	4.5	2064	36.0	13.69	67.5	4.970
-88.5	0.8927	-57.0	8.567	-25.5	42.38	6.0	1910	37.5	12.72	69.0	4.549
-87.0	0.9951	-55.5	8.856	-24.0	55.67	7.5	1708	39.0	11.79	70.5	4.170
-85.5	1.187	-54.0	8.990	-22.5	78.68	9.0	1470	40.5	11.05	72.0	3.767
-84.0	1.369	-52.5	9.088	-21.0	117.6	10.5	1213	42.0	10.43	73.5	3.432
-82.5	1.609	-51.0	9.104	-19.5	178.5	12.0	954.9	43.5	9.912	75.0	3.111
-81.0	1.947	-49.5	9.127	-18.0	269.4	13.5	709.1	45.0	9.497	76.5	2.786
-79.5	2.254	-48.0	9.181	-16.5	413.4	15.0	503.0	46.5	9.229	78.0	2.460
-78.0	2.594	-46.5	9.317	-15.0	605.5	16.5	329.6	48.0	9.078	79.5	2.137
-76.5	2.932	-45.0	9.513	-13.5	844.4	18.0	213.0	49.5	9.000	81.0	1.812
-75.0	3.249	-43.5	9.889	-12.0	1112	19.5	138.5	51.0	8.932	82.5	1.547
-73.5	3.581	-42.0	10.37	-10.5	1388	21.0	91.72	52.5	8.837	84.0	1.341
-72.0	3.964	-40.5	10.93	-9.0	1649	22.5	63.25	54.0	8.720	85.5	1.147
-70.5	4.349	-39.0	11.62	-7.5	1871	24.0	46.19	55.5	8.506	87.0	1.000
-69.0	4.762	-37.5	12.50	-6.0	2043	25.5	35.83	57.0	8.201	88.5	1.072
-67.5	5.182	-36.0	13.67	-4.5	2167	27.0	28.79	58.5	7.822	90.0	0.9637
-66.0	5.645	-34.5	15.05	-3.0	2246	28.5	23.90	60.0	7.369		
-64.5	6.180	-33.0	16.83	-1.5	2283	30.0	20.56	61.5	6.876		
-63.0	6.727	-31.5	19.19	0.0	2285	31.5	18.21	63.0	6.369		
-61.5	7.323	-30.0	22.40	1.5	2252	33.0	16.39	64.5	5.865		
-60.0	7.763	-28.5	27.03	3.0	2177	34.5	14.88	66.0	5.396		

Electricity Parameter:



Current I: 0.1000A Power: 3.380W
Voltage V: 33.79V PF: 1.000

Optical Parameter(Distance=2.410m):

Equivalent Luminous flux: $\Phi_{eff} = 393.0lm$ Efficiency: $Eff=116.29lm/W$
Diffuse angle: @ (25%): 29.6deg@ (50%): 22.6deg@ (75%): 15.9deg@ (50%): 22.6deg
Diffuse angle: @ (25%): 29.6deg@ (50%): 22.7deg@ (75%): 15.9deg@ (50%): 22.7deg
Imax=2287cd (C=0.0deg,G=-0.5deg) C0-180Plane Imax= 2287cd(G=-0.5deg)
C0-180Plane I0= 2285cd



GO1900L GONIOPHOTOMETER Test Report Page 1 Of 2

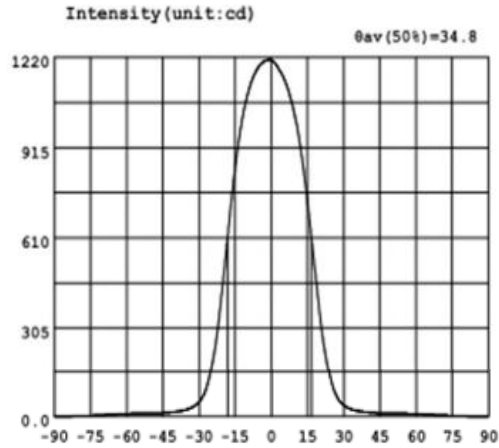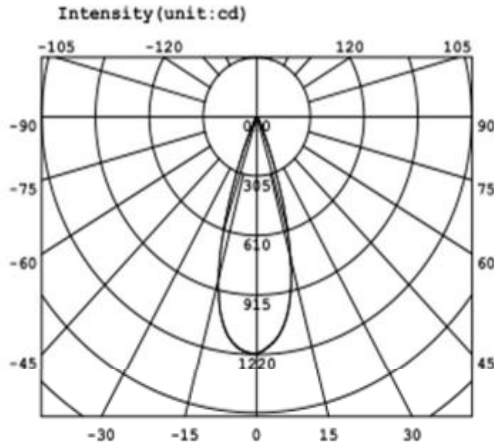

Intensity data:(deg , cd) C0-180

A	I	A	I	A	I	A	I	A	I	A	I
-90.0	1.028	-58.5	10.44	-27.0	96.53	4.5	1163	36.0	19.39	67.5	6.280
-88.5	1.096	-57.0	10.85	-25.5	142.6	6.0	1136	37.5	17.41	69.0	5.638
-87.0	1.255	-55.5	11.04	-24.0	203.8	7.5	1099	39.0	15.85	70.5	5.085
-85.5	1.503	-54.0	11.13	-22.5	282.7	9.0	1053	40.5	14.53	72.0	4.561
-84.0	1.774	-52.5	11.08	-21.0	385.6	10.5	995.7	42.0	13.49	73.5	4.143
-82.5	2.220	-51.0	11.08	-19.5	501.5	12.0	923.6	43.5	12.54	75.0	3.728
-81.0	2.375	-49.5	11.15	-18.0	621.4	13.5	834.5	45.0	11.82	76.5	3.334
-79.5	2.716	-48.0	11.37	-16.5	739.2	15.0	735.7	46.5	11.32	78.0	2.955
-78.0	3.049	-46.5	11.84	-15.0	846.2	16.5	625.2	48.0	11.01	79.5	2.580
-76.5	3.439	-45.0	12.54	-13.5	936.2	18.0	512.8	49.5	10.83	81.0	2.056
-75.0	3.881	-43.5	13.48	-12.0	1013	19.5	402.1	51.0	10.82	82.5	1.901
-73.5	4.368	-42.0	14.67	-10.5	1073	21.0	293.1	52.5	10.83	84.0	1.654
-72.0	4.921	-40.5	15.95	-9.0	1119	22.5	213.5	54.0	10.77	85.5	1.475
-70.5	5.565	-39.0	17.61	-7.5	1154	24.0	150.1	55.5	10.63	87.0	1.364
-69.0	6.240	-37.5	19.58	-6.0	1179	25.5	101.8	57.0	10.32	88.5	1.346
-67.5	6.863	-36.0	22.08	-4.5	1196	27.0	70.71	58.5	9.920	90.0	1.289
-66.0	7.498	-34.5	25.78	-3.0	1207	28.5	51.24	60.0	9.425		
-64.5	8.139	-33.0	31.18	-1.5	1213	30.0	39.16	61.5	8.845		
-63.0	8.757	-31.5	38.64	0.0	1212	31.5	31.07	63.0	8.236		
-61.5	9.372	-30.0	49.72	1.5	1202	33.0	25.64	64.5	7.592		
-60.0	9.949	-28.5	67.62	3.0	1183	34.5	21.93	66.0	6.949		

Electricity Parameter:



Current I: 0.1000A Power: 3.380W
Voltage V: 33.79V PF: 1.000

Optical Parameter(Distance=2.410m):

Equivalent Luminous flux: $\Phi_{eff} = 437.51m$ Efficiency: $Eff=129.46lm/W$
Diffuse angle: @ (25%): 42.9deg @ (50%): 34.8deg @ (75%): 26.1deg @ (50%): 34.8deg
Diffuse angle: @ (25%): 42.9deg @ (50%): 34.8deg @ (75%): 26.1deg @ (50%): 34.8deg
 $I_{max}=1213cd$ (C=0.0deg,G=-1.0deg) C0-180Plane $I_{max}= 1213cd$ (G=-1.0deg)
C0-180Plane $I_0= 1212cd$



GO1900L GONIOPHOTOMETER Test Report Page 1 Of 2

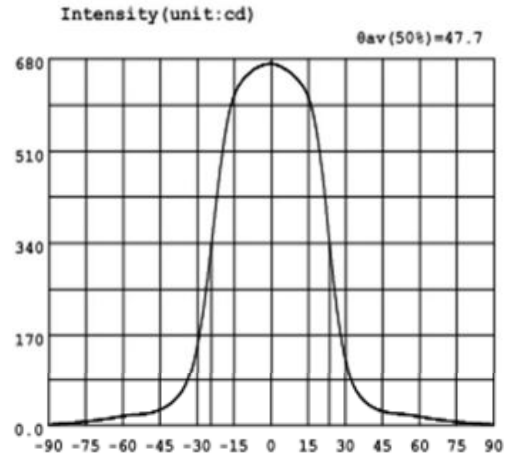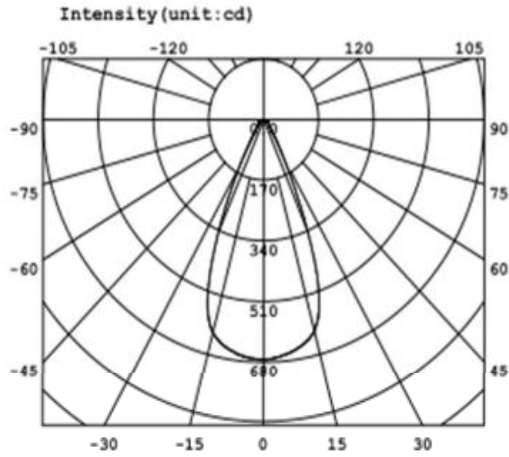

Intensity data:(deg , cd) C0-180


A	I	A	I	A	I	A	I	A	I	A	I
-90.0	2.076	-58.5	18.89	-27.0	234.6	4.5	664.6	36.0	54.94	67.5	11.27
-88.5	2.383	-57.0	19.73	-25.5	288.7	6.0	660.6	37.5	47.07	69.0	10.36
-87.0	3.021	-55.5	20.35	-24.0	347.9	7.5	656.0	39.0	40.92	70.5	9.595
-85.5	3.607	-54.0	20.75	-22.5	409.1	9.0	649.8	40.5	36.07	72.0	8.821
-84.0	4.116	-52.5	21.26	-21.0	466.8	10.5	643.1	42.0	32.38	73.5	8.099
-82.5	4.603	-51.0	21.93	-19.5	518.8	12.0	634.6	43.5	29.42	75.0	7.381
-81.0	5.155	-49.5	22.99	-18.0	561.0	13.5	624.1	45.0	27.10	76.5	6.766
-79.5	5.784	-48.0	24.62	-16.5	592.4	15.0	608.8	46.5	25.26	78.0	6.100
-78.0	6.401	-46.5	26.77	-15.0	614.2	16.5	586.3	48.0	23.91	79.5	5.624
-76.5	7.091	-45.0	29.46	-13.5	628.9	18.0	554.2	49.5	22.96	81.0	4.891
-75.0	7.854	-43.5	32.78	-12.0	639.2	19.5	509.2	51.0	22.31	82.5	4.355
-73.5	8.583	-42.0	36.66	-10.5	647.6	21.0	454.3	52.5	21.68	84.0	3.815
-72.0	9.361	-40.5	41.56	-9.0	653.9	22.5	386.5	54.0	20.98	85.5	3.264
-70.5	10.23	-39.0	47.57	-7.5	659.9	24.0	317.6	55.5	20.16	87.0	2.683
-69.0	11.10	-37.5	54.93	-6.0	664.2	25.5	255.4	57.0	19.12	88.5	2.326
-67.5	12.01	-36.0	64.23	-4.5	667.4	27.0	201.7	58.5	18.03	90.0	1.947
-66.0	13.03	-34.5	76.93	-3.0	669.6	28.5	157.8	60.0	16.83		
-64.5	14.16	-33.0	94.17	-1.5	671.3	30.0	123.7	61.5	15.61		
-63.0	15.34	-31.5	118.0	0.0	671.8	31.5	97.71	63.0	14.41		
-61.5	16.61	-30.0	149.2	1.5	670.5	33.0	78.88	64.5	13.31		
-60.0	17.82	-28.5	189.5	3.0	667.9	34.5	65.14	66.0	12.27		


Electricity Parameter:


Current I: 0.1000A Power: 4.170W
Voltage V: 41.70V PF: 1.000


Optical Parameter(Distance=2.559m):


Equivalent Luminous flux: $\Phi_{eff} = 475.8lm$ Efficiency: $Eff=114.12lm/W$
Diffuse angle: @ (25%): 57.3deg@ (50%): 47.7deg@ (75%): 39.5deg@ (50%): 47.7deg
Diffuse angle: @ (25%): 57.3deg@ (50%): 47.7deg@ (75%): 39.5deg@ (50%): 47.7deg
 $I_{max}=671.9cd$ (C=0.0deg, G=-0.5deg) C0-180Plane $I_{max}= 671.9cd$ (G=-0.5deg)
C0-180Plane $I_{0}= 671.8cd$

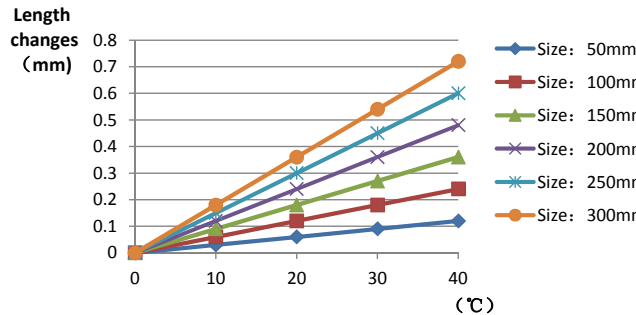		Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Judgment	Remarks																																										
1.Size	highly	29.5			29.46	29.46	29.46	29.44		Test environment : In 20℃ - 25℃ environment to achieve thermal equilibrium after the test.																																										
	The diameter of	62			61.89	61.9	61.87	61.87																																												
	The thickness of the	2.5			2.54	2.6	2.54	2.52																																												
	Gate shear can not affect the appearance of the lamp																																																			
See attachment "Appearance Inspection Standards"																																																				
2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr	No burr	No burr	OK																																											
			No stains	No stains	No stains	No stains	No stains																																													
3.Material	PMMA				Color	Transparent			OK																																											
4.Optical index	Testing LED	D9																																																		
	The size and rated power of the light-emitting surface (LES) of the COB recommended by this lens should conform to the parameters in the product basic information table. if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.																																																			
	FWHM	See light distribution curve																																																		
	K-value (CD/LM)				11.8	11.7	11.8	11.8																																												
	angle				13.2°	13.3°	13.5°	13.4°																																												
	Efficiency				93.70%	95.30%	94.80%	95.70%																																												
Facula	See the signature sample																																																			
Comprehensive judgment	Qualified																																																			
Remarks:	<p>1、 Tool Number: V-Vernier Caliper 2D-Quadratic H-Height Gauge M-Tool Microscope P-Needle T-Thick Gauge R-Radius Gauge E-Visual.</p> <p>2、 Ambient temperature on the size of the product refer to the table on the right</p>																																																			
	<p style="text-align: center;">PMMA product size changes with temperature table</p>  <table border="1"> <caption>PMMA product size changes with temperature table</caption> <thead> <tr> <th>Temperature (°C)</th> <th>Size: 50mm</th> <th>Size: 100mm</th> <th>Size: 150mm</th> <th>Size: 200mm</th> <th>Size: 250mm</th> <th>Size: 300mm</th> </tr> </thead> <tbody> <tr> <td>0</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> </tr> <tr> <td>10</td> <td>0.05</td> <td>0.08</td> <td>0.12</td> <td>0.15</td> <td>0.18</td> <td>0.22</td> </tr> <tr> <td>20</td> <td>0.10</td> <td>0.15</td> <td>0.22</td> <td>0.28</td> <td>0.35</td> <td>0.42</td> </tr> <tr> <td>30</td> <td>0.15</td> <td>0.22</td> <td>0.30</td> <td>0.38</td> <td>0.48</td> <td>0.58</td> </tr> <tr> <td>40</td> <td>0.20</td> <td>0.28</td> <td>0.38</td> <td>0.48</td> <td>0.60</td> <td>0.72</td> </tr> </tbody> </table>										Temperature (°C)	Size: 50mm	Size: 100mm	Size: 150mm	Size: 200mm	Size: 250mm	Size: 300mm	0	0.00	0.00	0.00	0.00	0.00	0.00	10	0.05	0.08	0.12	0.15	0.18	0.22	20	0.10	0.15	0.22	0.28	0.35	0.42	30	0.15	0.22	0.30	0.38	0.48	0.58	40	0.20	0.28	0.38	0.48	0.60	0.72
Temperature (°C)	Size: 50mm	Size: 100mm	Size: 150mm	Size: 200mm	Size: 250mm	Size: 300mm																																														
0	0.00	0.00	0.00	0.00	0.00	0.00																																														
10	0.05	0.08	0.12	0.15	0.18	0.22																																														
20	0.10	0.15	0.22	0.28	0.35	0.42																																														
30	0.15	0.22	0.30	0.38	0.48	0.58																																														
40	0.20	0.28	0.38	0.48	0.60	0.72																																														
Precautions:	<p>1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.</p> <p>2. Try to avoid touching the total reflection surface when taking the lens.</p> <p>3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).</p> <p>4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.</p>																																																			

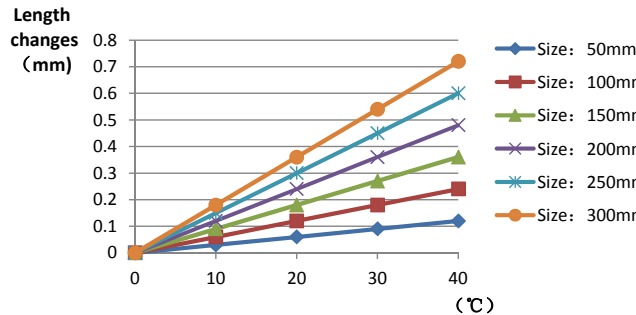		Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Judgment	Remarks																																										
1.Size	highly	29.5			29.52	29.58	29.48	29.48		Test environment : In 20℃ - 25℃ environment to achieve thermal equilibrium after the test.																																										
	The diameter of	62			61.88	61.89	61.85	61.87																																												
	The thickness of the	2.5			2.62	2.64	2.53	2.56																																												
	Gate shear can not affect the appearance of the lamp																																																			
See attachment "Appearance Inspection Standards"																																																				
2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr	No burr	No burr	OK																																											
			No stains	No stains	No stains	No stains	No stains																																													
3.Material	PMMA				Color	Transparent			OK																																											
4.Optical index	Testing LED	D9																																																		
	The size and rated power of the light-emitting surface (LES) of the COB recommended by this lens should conform to the parameters in the product basic information table. if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.																																																			
	FWHM	See light distribution curve																																																		
	K-value (CD/LM)				5.8	6	6	5.8																																												
	angle				22.6°	22.1°	22.2°	22.4																																												
	Efficiency				95.40%	95.40%	94.60%	95.00%																																												
Facula	See the signature sample																																																			
Comprehensive judgment	Qualified																																																			
Remarks:	<p>1、 Tool Number: V- Vernier Caliper 2D- Quadratic H-Height Gauge M-Tool Microscope P-Needle T- Thick Gauge R-Radius Gauge E-Visual.</p> <p>2、 Ambient temperature on the size of the product refer to the table on the right</p>																																																			
	<p style="text-align: center;">PMMA product size changes with temperature table</p>  <table border="1"> <caption>PMMA product size changes with temperature table</caption> <thead> <tr> <th>Temperature (°C)</th> <th>Size: 50mm</th> <th>Size: 100mm</th> <th>Size: 150mm</th> <th>Size: 200mm</th> <th>Size: 250mm</th> <th>Size: 300mm</th> </tr> </thead> <tbody> <tr> <td>0</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> </tr> <tr> <td>10</td> <td>0.05</td> <td>0.08</td> <td>0.12</td> <td>0.15</td> <td>0.18</td> <td>0.22</td> </tr> <tr> <td>20</td> <td>0.10</td> <td>0.15</td> <td>0.22</td> <td>0.28</td> <td>0.35</td> <td>0.42</td> </tr> <tr> <td>30</td> <td>0.15</td> <td>0.22</td> <td>0.30</td> <td>0.38</td> <td>0.48</td> <td>0.58</td> </tr> <tr> <td>40</td> <td>0.20</td> <td>0.28</td> <td>0.38</td> <td>0.48</td> <td>0.60</td> <td>0.72</td> </tr> </tbody> </table>										Temperature (°C)	Size: 50mm	Size: 100mm	Size: 150mm	Size: 200mm	Size: 250mm	Size: 300mm	0	0.00	0.00	0.00	0.00	0.00	0.00	10	0.05	0.08	0.12	0.15	0.18	0.22	20	0.10	0.15	0.22	0.28	0.35	0.42	30	0.15	0.22	0.30	0.38	0.48	0.58	40	0.20	0.28	0.38	0.48	0.60	0.72
Temperature (°C)	Size: 50mm	Size: 100mm	Size: 150mm	Size: 200mm	Size: 250mm	Size: 300mm																																														
0	0.00	0.00	0.00	0.00	0.00	0.00																																														
10	0.05	0.08	0.12	0.15	0.18	0.22																																														
20	0.10	0.15	0.22	0.28	0.35	0.42																																														
30	0.15	0.22	0.30	0.38	0.48	0.58																																														
40	0.20	0.28	0.38	0.48	0.60	0.72																																														
Precautions:	<p>1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.</p> <p>2. Try to avoid touching the total reflection surface when taking the lens.</p> <p>3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).</p> <p>4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.</p>																																																			

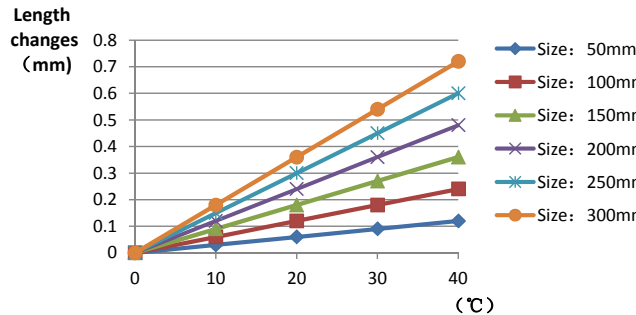	Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Judgment	Remarks																																										
1.Size	highly	29.5		29.5	29.51	29.42	29.42		Test environment : In 20℃ - 25℃ environment to achieve thermal equilibrium after the test.																																										
	The diameter of	62		61.88	61.85	61.9	61.86																																												
	The thickness of the	2.5		2.5	2.46	2.48	2.46																																												
	Gate shear can not affect the appearance of the lamp																																																		
See attachment "Appearance Inspection Standards"																																																			
2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr		OK																																											
			No stains	No stains	No stains	No stains																																													
3.Material	PMMA			Color	Transparent			OK																																											
4.Optical index	Testing LED	D9																																																	
	The size and rated power of the light-emitting surface (LES) of the COB recommended by this lens should conform to the parameters in the product basic information table. if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.																																																		
	FWHM	See light distribution curve																																																	
	K-value (CD/LM)			2.8	2.7	2.7	2.7																																												
	angle			34.8°	35.1°	35.5°	36.1°																																												
	Efficiency			95.00%	95.00%	95.30%	93.80%																																												
Facula	See the signature sample																																																		
Comprehensive judgment	Qualified																																																		
Remarks:	<p>1、 Tool Number: V- Vernier Caliper 2D- Quadratic H-Height Gauge M-Tool Microscope P-Needle T- Thick Gauge R-Radius Gauge E-Visual.</p> <p>2、 Ambient temperature on the size of the product refer to the table on the right</p>																																																		
	<p style="text-align: center;">PMMA product size changes with temperature table</p>  <table border="1"> <caption>PMMA product size changes with temperature table</caption> <thead> <tr> <th>Temperature (°C)</th> <th>Size: 50mm</th> <th>Size: 100mm</th> <th>Size: 150mm</th> <th>Size: 200mm</th> <th>Size: 250mm</th> <th>Size: 300mm</th> </tr> </thead> <tbody> <tr> <td>0</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> </tr> <tr> <td>10</td> <td>0.05</td> <td>0.08</td> <td>0.12</td> <td>0.15</td> <td>0.18</td> <td>0.22</td> </tr> <tr> <td>20</td> <td>0.10</td> <td>0.15</td> <td>0.22</td> <td>0.28</td> <td>0.35</td> <td>0.42</td> </tr> <tr> <td>30</td> <td>0.15</td> <td>0.22</td> <td>0.30</td> <td>0.38</td> <td>0.48</td> <td>0.58</td> </tr> <tr> <td>40</td> <td>0.20</td> <td>0.28</td> <td>0.38</td> <td>0.48</td> <td>0.60</td> <td>0.72</td> </tr> </tbody> </table>									Temperature (°C)	Size: 50mm	Size: 100mm	Size: 150mm	Size: 200mm	Size: 250mm	Size: 300mm	0	0.00	0.00	0.00	0.00	0.00	0.00	10	0.05	0.08	0.12	0.15	0.18	0.22	20	0.10	0.15	0.22	0.28	0.35	0.42	30	0.15	0.22	0.30	0.38	0.48	0.58	40	0.20	0.28	0.38	0.48	0.60	0.72
Temperature (°C)	Size: 50mm	Size: 100mm	Size: 150mm	Size: 200mm	Size: 250mm	Size: 300mm																																													
0	0.00	0.00	0.00	0.00	0.00	0.00																																													
10	0.05	0.08	0.12	0.15	0.18	0.22																																													
20	0.10	0.15	0.22	0.28	0.35	0.42																																													
30	0.15	0.22	0.30	0.38	0.48	0.58																																													
40	0.20	0.28	0.38	0.48	0.60	0.72																																													
Precautions:	<p>1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.</p> <p>2. Try to avoid touching the total reflection surface when taking the lens.</p> <p>3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).</p> <p>4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.</p>																																																		




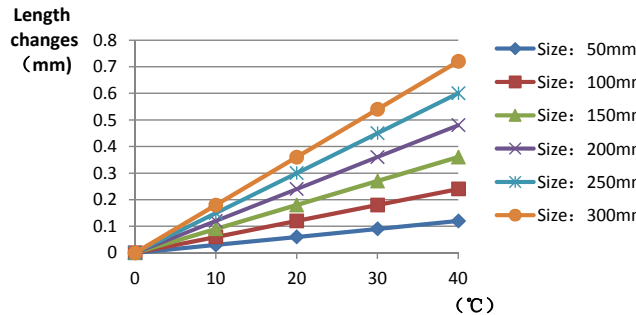
		Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Judgment	Remarks																																										
1.Size	highly	29.5			29.47	29.56	29.49	29.58		Test environment : In 20℃ - 25℃ environment to achieve thermal equilibrium after the test.																																										
	The diameter of	62			62	62.06	62.03	62.02																																												
	The thickness of the	2.5			2.62	2.62	2.62	2.63																																												
	Gate shear can not affect the appearance of the lamp																																																			
See attachment "Appearance Inspection Standards"																																																				
2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr	No burr	No burr	OK																																											
			No stains	No stains	No stains	No stains	No stains																																													
3.Material	PMMA				Color	Transparent			OK																																											
4.Optical index	Testing LED	D9																																																		
	The size and rated power of the light-emitting surface (LES) of the COB recommended by this lens should conform to the parameters in the product basic information table. if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.																																																			
	FWHM	See light distribution curve																																																		
	K-value (CD/LM)				1.7	1.4	1.4	1.4																																												
	angle				47.7°	47.7°	47.6°	47.2°																																												
	Efficiency				88.70%	89.00%	89.00%	89.30%																																												
Facula	See the signature sample																																																			
Comprehensive judgment	Qualified																																																			
Remarks:	<p>1、 Tool Number: V-Vernier Caliper 2D-Quadratic H-Height Gauge M-Tool Microscope P-Needle T-Thick Gauge R-Radius Gauge E-Visual.</p> <p>2、 Ambient temperature on the size of the product refer to the table on the right</p>																																																			
	<p style="text-align: center;">PMMA product size changes with temperature table</p>  <table border="1"> <caption>PMMA product size changes with temperature table</caption> <thead> <tr> <th>Temperature (°C)</th> <th>Size: 50mm</th> <th>Size: 100mm</th> <th>Size: 150mm</th> <th>Size: 200mm</th> <th>Size: 250mm</th> <th>Size: 300mm</th> </tr> </thead> <tbody> <tr> <td>0</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> <td>0.00</td> </tr> <tr> <td>10</td> <td>0.05</td> <td>0.08</td> <td>0.12</td> <td>0.15</td> <td>0.18</td> <td>0.22</td> </tr> <tr> <td>20</td> <td>0.10</td> <td>0.15</td> <td>0.22</td> <td>0.28</td> <td>0.35</td> <td>0.42</td> </tr> <tr> <td>30</td> <td>0.15</td> <td>0.22</td> <td>0.30</td> <td>0.38</td> <td>0.48</td> <td>0.58</td> </tr> <tr> <td>40</td> <td>0.20</td> <td>0.28</td> <td>0.38</td> <td>0.48</td> <td>0.60</td> <td>0.72</td> </tr> </tbody> </table>										Temperature (°C)	Size: 50mm	Size: 100mm	Size: 150mm	Size: 200mm	Size: 250mm	Size: 300mm	0	0.00	0.00	0.00	0.00	0.00	0.00	10	0.05	0.08	0.12	0.15	0.18	0.22	20	0.10	0.15	0.22	0.28	0.35	0.42	30	0.15	0.22	0.30	0.38	0.48	0.58	40	0.20	0.28	0.38	0.48	0.60	0.72
Temperature (°C)	Size: 50mm	Size: 100mm	Size: 150mm	Size: 200mm	Size: 250mm	Size: 300mm																																														
0	0.00	0.00	0.00	0.00	0.00	0.00																																														
10	0.05	0.08	0.12	0.15	0.18	0.22																																														
20	0.10	0.15	0.22	0.28	0.35	0.42																																														
30	0.15	0.22	0.30	0.38	0.48	0.58																																														
40	0.20	0.28	0.38	0.48	0.60	0.72																																														
Precautions:	<p>1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.</p> <p>2. Try to avoid touching the total reflection surface when taking the lens.</p> <p>3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).</p> <p>4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.</p>																																																			

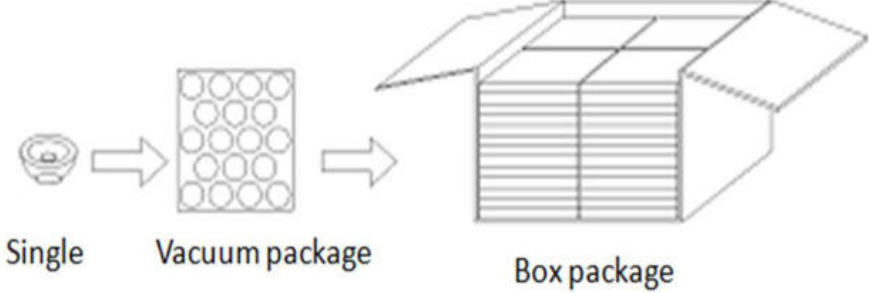PN		HK-HG-62@30-15-D9-21-1g-1		Product Name	HK Dark 62@30-15 degree lens		
Product material		PMMA					
Package diagram		 <p style="text-align: center;"> Single Vacuum package Box package </p>					
Product packing		9	A/ Box	4	pcs/Layer		
		9	Layer/Box	324	A/ Carton		
Packaging Materials	NO.	Part No	Part name	Size	Dosage	Unit	Remarks
	1	2. 07. 0078	Blister box	23cm*21cm	36	BAG	
	2	2. 08. 0001	PE film	25cm*27cm	36	PCS	
	3	2. 06. 0005	Reel label paper	62mm*42mm	36	PCS	
	4	2. 06. 0005	Box label paper	62mm*70mm	1	PCS	
	5	2. 06. 0003	big plate	46cm*42cm	10	PCS	
	6	2. 06. 0011	big flat carton	48cm*44cm*37cm	1	PCS	
Remarks	The loose packing is not subject to this specification. Customer's requirements shall prevail						

Special notice

When glue pass through holes, columns and other structures, or part of the thin structure, will form a weld line. The product which uses multi-point injection welding line will appear because of the combination of sol, as shown below:

Syntner

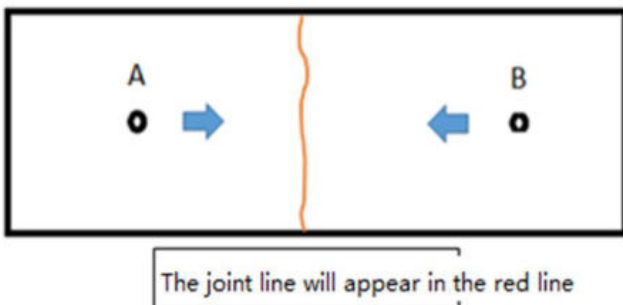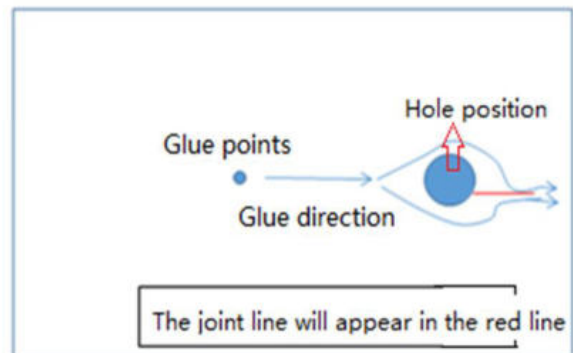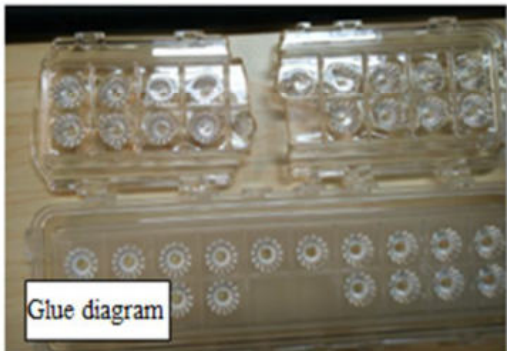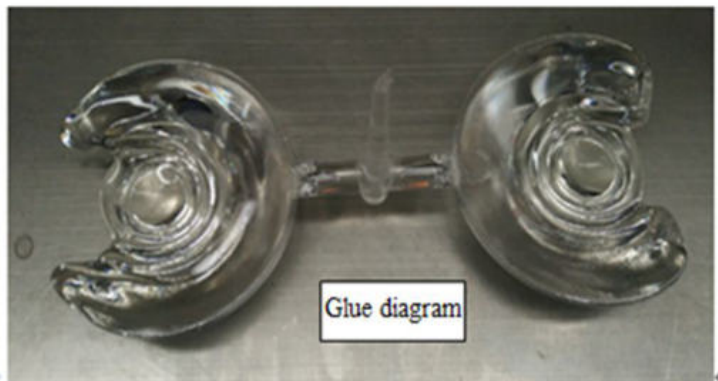

Please note :

The appearance of lines in the structure of the product as well as at the screw hole is a normal phenomenon, will not affect the actual use of the product, and can not be avoided at this stage.

Appearance inspection standards

1 Operating procedures

1.1.1 Sampling standards, sampling plan and AQL

Test level : GB/T2828.1-2012 The first part is according to the acceptance quality limit (AQL) retrieval batch inspection sampling plan, general inspection level II level, CR class defect coefficient 0, MA defect rejection level AQL = 0.65, MI class defect rejection level AQL = 1.0; defect level please see 5.4.

2 Code table

Code	Code description	Unit	Code		Code description	Unit
N	Amount/pcs	pcs	D		Diameter	mm
L	Length	mm	H		Depth	mm
W	Width	mm	DS		Distance	mm
S	Proportion	mm ²	SS		Offset	mm

3 Test conditions

3.1 Sight distance and working hours: Sight distance should be 30-35cm, each side of the inspection time does not exceed 12s, the visual angle of 45-135 degrees;

3.2 Light: 2x40w cool white fluorescent lamp, the light source is 500-550mm away from the lens surface; in order to make the appearance defect can be correctly recognized, the illumination should be 500-1000Lux, and the observation time is 10 seconds.

3.3 Visual inspection staff should be 1.0 (including corrected visual acuity) above, no color blindness, color weakness.

4 Appearance inspection standards

Test items	Judging standard	Inspection equipment	Defect level		
		Testing method	MI	MA	CR
Check the sample	When start the machine and process, all products have to check the appearance of the sample, the appearance of the sample is divided into qualified samples and limited samples.	Sample comparison , visual			
	1: Qualified sample refers to the appearance and structure standard of the product which recognized by the client, the sample size should be confirmed before mass production;				

	2: The limited sample refers to the limit of a particular exceptionally developed sample. Limit the sample only for its specific point of exception to confirm; The priority is higher than the other criteria in this table. When there is a limited sample, the limit sample shall prevail.				
Raw edge	Not allowed to affect the size and assembly	Visual, point card		√	
Scratch	1: Non-optical surface and non-exposed surface scratches should be visually insignificant and the length is less than 1/10 of the maximum surface size.	Visual, point card, calipers		√	
Fingerprint	Fingerprints are not allowed on all products	Visual		√	
Foreign objects, black spots, white spots	The product may not be attached to foreign objects, including oil, fiber, dregs of water gap and so on				√
Deformation	Insufficient filling shall not affect the appearance of the assembly and the exposed surfaces.	Visual, feeler			√
Poor ejection	Products may not appear bad ejection, including no convex top, thimble printed on the assembly surface shall not be higher than the product surface, non-assembled surface thimble height should not exceed the product size tolerances; thimble printing should be less than the product surface and no more than 0.3; thimble surface treatment should be consistent with the product side.	Visual, point card		√	
	Ejection strain: the optical surface and the appearance of the exposed surface after assembly are not allowed to have a strain, and the structural surface does not allow visual obvious strain.				
Insufficient filling	Insufficient filling shall not affect the appearance of the assembly and the exposed surfaces , The signature sample shall prevail.	Visual, point card		√	
Shrink	When the entire surface of the product shrinks, the optical properties and dimensions must meet the requirements, and the visual will not significantly affect the appearance.Part shrink reference point defects	Visual, point card		√	
Flow marks、Welding line	1 : Product does not allow the presence of flow marks and welding lines unless the structure can not be avoided;	Visual		√	
	2: The remaining flow marks shall not appear in the optical surface, a single L ≤ 10mm, no more than two				

Bubble	No bubbles are allowed	Visual		√	
Foreign objects, black spots, white spots	Not obvious or $D \leq 0.3\text{mm}$ black spots and foreign bodies in the area of 100x100mm not more than 1; Exceeded foreign matter black spots is judged bad.	Visual, point card	√		
Damaged	No damage is allowed	Visual			√
Cold glue	Optical surface may not have cold glue, non-optical surface cold glue should meet the visual is not obvious.	Visual	√		
Bad incision	1: Do not affect the product size, shall not penetrate the optical surface, the cut should be smooth;	Visual			√
	2: Laser cutting products, the optical surface burns shall not occur after the processing is completed. Beading must not affect product installation				
	3: Three molds and hot runner gate shall not appear residue.				
Scrub	Scrub surface should be uniform, off the scrub phenomenon should not be obvious , A single off scrub imprint requires $D \leq 1\text{ mm}$ and no more than 1 area within a 50x50 mm area	Visual		√	