

Chengdu HercuLux Photoelectric Technology Co.,Ltd **Product Approval**

Approval number:

Customer:

Manufacturer: Chengdu HercuLux Photoelectric Technology Co.,Ltd

PN	Code	Product
HK-RG-75@35-15-D14-21-1g-1	1. 01. 23071	HK Moony 75@35-15° lens
HK-RG-75@35-24-D14-21-1g-1	1. 01. 12977	HK Moony 75@35-24° lens
HK-RG-75@35-36-D14-21-1g-1	1. 01. 13027	HK Moony 75@35-36° lens
HK-RG-75@35-50-D14-21-1g-1	1. 01. 13037	HK Moony 75@35-50° lens



	Supplier	confirmatio	n		Client con	firmation	
Proposed		DATE		Qualified□			
Project manager		DATE		Unqualified□		DATE	
Audit				Audit		DATE	
Approved		DATE		Approved		DATE	
Stamp		DATE		Stamp		DATE	

(Confirmation of acceptance by both parties must be signed and sealed)

Factory: Chengdu Shuangliu District, lot industrial park 2 road HercuLux Photoelectric Park

Phone: 028-85887727 (801) 028-85887990 (801) Fax: 028-85887730 http://www.herculux.cn/

Sales Dept: Shenzhen Nanshan District Nanshan Cloud Valley Innovation Industrial Park Comprehensive Service Building, 501-505

TEL: 0755-2937 1541 FAX: 0755-2907 5140

^{*}Approval In duplicate, for both supplier and customer.




HERCULUX Product Approval

TEL: 0755-2937 1541 Date updated: 2022/8/1 FAX: 0755-2907 5140 http://www.herculux.cn/

Product Picture:	
PN:	HK-RG-75@35-15-D14-21-1g-1
Size(L*W*H/Φ*H):	Ф:75mm; H:35.1mm
Material:	PC
Effiency:	\
Temperature(Topr):	Material extreme temperature resistance: -40°C to +120°C long-term use temperature: -40°C to +100°C
FWHM:	15°、24°、36°、50°



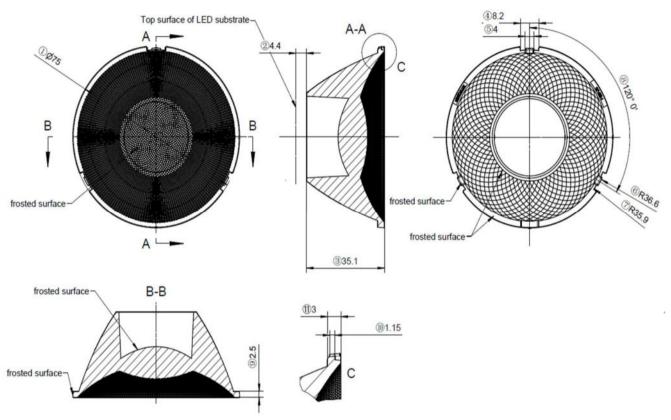


- 1. The 3D map is not indicated for rounded corners and draft angle.
- 2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
- 3, The surface has no flash, shrinkage, bubbles and other defects.
- *4. When the lamp adopts rubber ring for waterproofing: the roughness of the contact surface between the radiator and the rubber ring is required: $Ra<3.2\mu m$

Ī	Optical	design							ŀ	HK-RG-7	'5@35-15-D14	-21-1g-1	1
Ī	tructur	ucture desig Review					HK Moon	y 75@35-15°lens			1.01.23071		
Ī	Rov	iow							umber o	f drawin	qty	wei	ight
L	nev	iew											
	Validation			Material:	PC	CDHK							
~250 250~450 >450													

							,	alluation				iviaterial:	FC	CDIIK
MT5 Tolerance	Basic size	<3	3∼10	10~24	24~65	65~140	140~2	50 250	~450	>450	0			
	olerance valu	±0.1	±0.15	±0.2	±0.35	±0.50	±0.80	±	L.2	±2.0)			



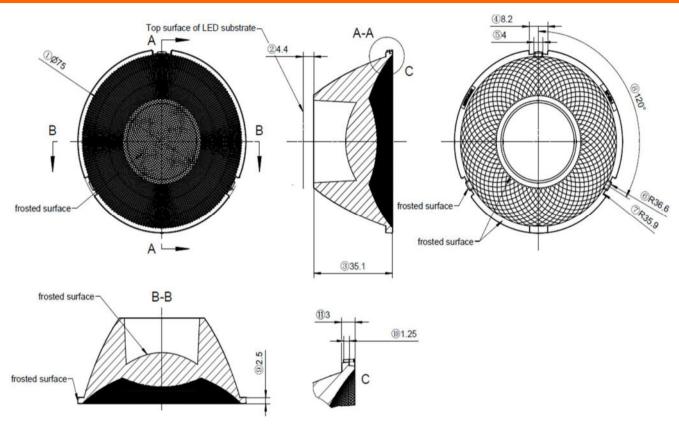


- 1. The 3D map is not indicated for rounded corners and draft angle.
- 2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
- 3, The surface has no flash, shrinkage, bubbles and other defects.
- *4. When the lamp adopts rubber ring for waterproofing: the roughness of the contact surface between the radiator and the rubber ring is required: Ra<3.2 μ m

	Optical	design							Н	K-RG-7	5@35-24-D14-	21-1g-1	1
	tructur	ucture desig					HK Moon	y 75@35-24°lens			1.01.12977		
r	Rev	iew							umber of	drawin	qty	wei	ight
	Validation					Material:	PC			CDHK			
)^	~250	250~	~450	>4	450								

							van	dation			Widterial.	16	CBTIK
MT5 Tolerance	Basic size	<3	3~10	10~24	24~65	65~140	140~250	250~45	>4	50			
	olerance valu	±0.1	±0.15	±0.2	±0.35	±0.50	±0.80	±1.2	±2	.0			



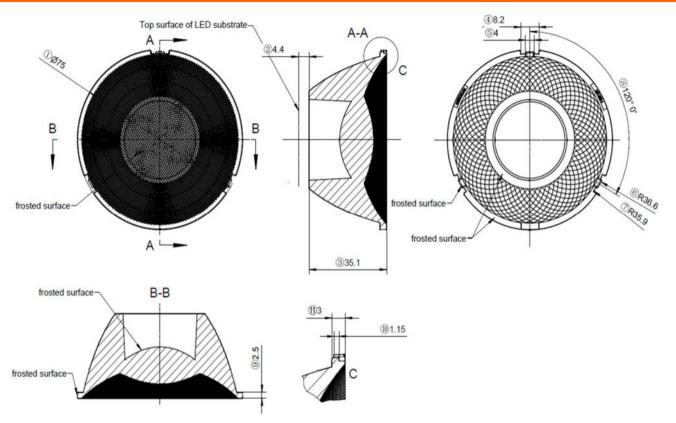


- 1. The 3D map is not indicated for rounded corners and draft angle.
- 2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
- 3, The surface has no flash, shrinkage, bubbles and other defects.
- *4. When the lamp adopts rubber ring for waterproofing: the roughness of the contact surface between the radiator and the rubber ring is required: $Ra<3.2\mu m$

	Optical	design						ŀ	HK-RG-7	'5@35-36-D14	-21-1g-1	l
	tructur	ructure desig				HK Moon	y 75@35-36°lens			1.01.13027		
	Dov	Review						umber o	f drawin	qty	wei	ght
	Kev	iew										
	Valid	Validation		Material:	PC	CDHK						
)^	~250 250~450 >450											

							• • •	naation				 naterial.	10	CDTIK
MT5 Tolerance	Basic size	<3	3∼10	10~24	24~65	65~140	140~250	250	~450	>4!	50			
	olerance valu	±0.1	±0.15	±0.2	±0.35	±0.50	±0.80	±1	L.2	±2.	.0			



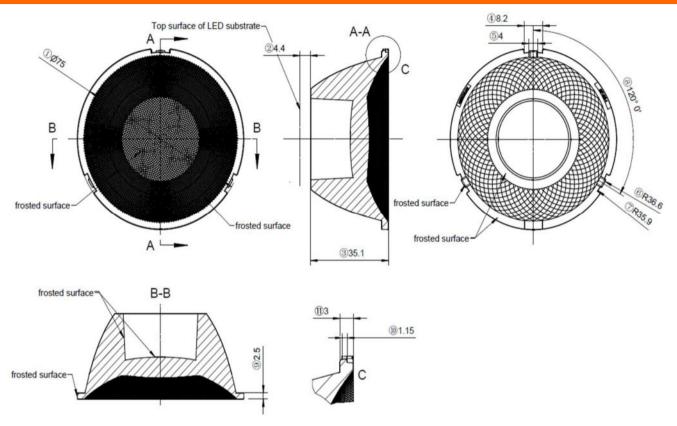


- 1. The 3D map is not indicated for rounded corners and draft angle.
- 2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
- 3, The surface has no flash, shrinkage, bubbles and other defects.
- *4. When the lamp adopts rubber ring for waterproofing: the roughness of the contact surface between the radiator and the rubber ring is required: $Ra<3.2\mu m$


	Optical	design						HK-RG-	75@35-50-D14	-21-1g-1	
	tructur	e desig				HK Moon	y 75@35-50°lens		1.01.13037		
	Rev	riew						umber of drawir	qty	weigh	nt
	Validation			Material:	PC		CDHK				
)^	~250	250~	~450	>4	450						
^	00	1	1								

								vanaatie				···ateriai.	
MT5 Tolerance	Basic size	<3	3∼10	10~24	24~65	65~140	140~	250 2	50~450	>4	50		
	olerance valu	±0.1	±0.15	±0.2	±0.35	±0.50	±0.8	30	±1.2	±2	.0		


IES----

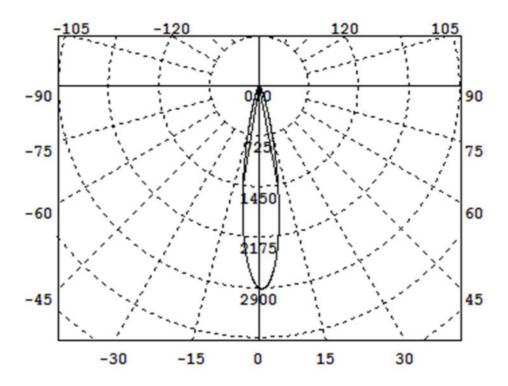


IES----

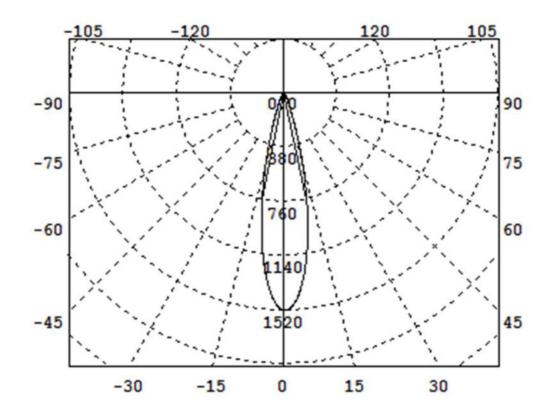



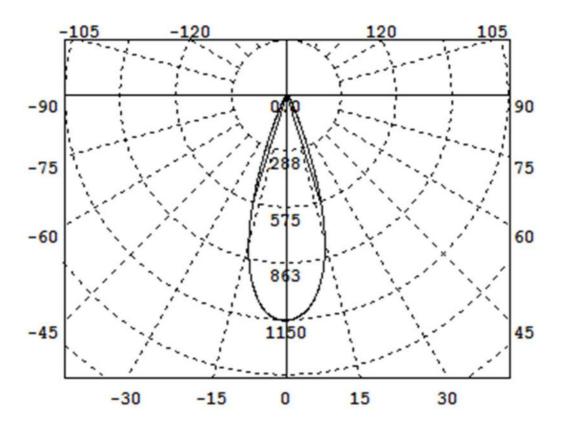



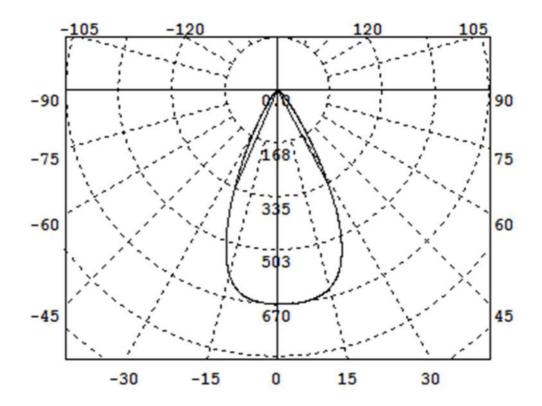



			Standard size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Jud gme nt	Remarks
	diame	ter	75			75. 04	75. 02	74. 98	74. 97		Test environment: In 20 °C -25 °C
1.Size	heigl	ht	35.1			35. 27	35. 3	35. 29	35. 27		environment to achieve thermal
	thickn	ess	2.5			2.65	2. 66	2.65	2.66		equilibrium after the test.
				Gate s	hear can r	not affect t	ne appearai	nce of the I	amp		
				See a	ttachment	"Appearai	nce Inspecti	ion Standa	rds"		T
2.Appear	ance		See achment pearance	E	1	No burr	No burr	No burr	No bu	rr	OK
Quality		Ins	spection andards"		N	o stains	No stains	No stains	No stai	ins	
3.Materia	ıl			PC			Color	Tra	ınsparent		OK
	Testing						EN CLU-03 ght source r				
4.Optica I index		ty of IM e				ns of the ι	be out of rause environment distribution 20. 1	ment, the le			dissipation Ily tested and
	Effici			_							$\overline{}$
	Facula	See	the signatu	re sample		,				J	
Compreh judgm						•	(Qualified			
Remarks 1、Tool I Vernier C Quadratic M-Tool M Needle T Radius C 2、Ambi on the siz refer to th right	: Number: Caliper 2 C H-Heiç Iicrosco -Thick C auge E- ent tem ze of the	D- ght Gape P- Gauge Visua perate proce	e R- al. ure luct	Lengtl change (mm	n es _{0.8 —}	oduct size	table table		Size: Size: 100mi Size: 150mi X Size: 200mi	m m	1

Precautions

- 1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.
- 2. Try to avoid touching the total reflection surface when taking the lens.
- 3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).
- 4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.



			Standar d size	Upper Size	Lower size	Test result1	Test	Test	Test	Test result5	Test	Test result7	Test	Jud gme	Remarks
			u size	limit	limit	result i	resuitz	results	result4	resulto	resulto	resuit/	resulto	nt	Test
	diame	ter	75			75.04	75.06	75	75.01	75.1	74.94	74.99	75.07		environment: In 20 °C -25
1.Size	heig	ht	35.1			35.17	35.3	35.2	35.15	35.25	35.23	35.2	35.23		°C environment
	thickr	ness	2.5			2.64	2.63	2.64	2.64	2.68	2.66	2.64	2.68		to achieve thermal
					Gate s	hear car	n not aff	ect the a	ippearai	nce of th	e lamp				
		T			See a	ttachme	nt "Appe	earance	Inspecti	on Stan	dards"	ı			
2.Appea	rance	atta	See chment earance	E		No bu	ırr	No	burr	No	burr	1	No burr		OK
Quality	Ins		pection ndards"	1		No sta	stains		tains	No s	tains	N	o stains		
3.Materia	al			Р	С			Co	olor		Tra	ansparer	nt		OK
	Testing	LED					(CITIZEN	CLU-03	38-1205					
	The recommended size and power ra source of the test, if it is required to be conditions of the use envir					ut of ran	ge. Acco	ording to nould be	the hea	at dissipa sted and	ation cap tested t	oability o	f the lan	np an	
4.Optic	FWHM						S	ee light o	distributi	on curve	e	1	1		
al index				23. 7		23. 6	23.8	24.1	24. 5	24. 1	24	24. 2			
	K-value (CD/LM)														
	Effici	Efficiency													
	Facula	See tl	he signati	ure samp	le		`								
Compre judgr							Qualified								
Remarks: 1. Tool Number: V- Vernier Caliper 2D- Quadratic H-Height Gauge M-Tool Microscope P- Needle T-Thick Gauge R- Radius Gauge E-Visual. 2. Ambient temperature on the size of the product refer to the table on the right PC prod Length changes (mm) 0.6 0.4 0.2 0 0 0			duct size	e chang	res with			Size:	200mm 250mm						

Precautions

- 1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.
- 2. Try to avoid touching the total reflection surface when taking the lens.
- 3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).
- 4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.



			Standar d size	Upper Size limit	Lower size limit	Test result1	Test result2	Test result3	Test result4	Test result5	Test result6	Test result7	Test result8	Jud gme nt	Remarks
	diame	ter	75			74.87	74.84	74.85	74.84	74.84	74.78	74.79	74.8		environment:
1.Size	heig	ht	35.1			35.15	35.14	35.15	35.1	35.21	35.19	35.17	35.19		In 20 °C -25 °C
	thickness		2.5			2.57	2.56	2.56	2.51	2.61	2.59	2.58	2.62		environment to achieve thermal
					Gate	shear ca	n not aff	ect the	appeara	nce of t	he lamp				пстпа
					See a	attachme	ent "App	earance	Inspect	tion Star	ndards"				
2.Appea	ırance	atta	See chment earance	E		No bu	ırr	No	burr	No	burr	1	No burr		OK
Quality		Ins	pection ndards"	J		No sta	ins	No s	tains	No s	tains	N	o stains	i	Öl
3.Materi	al			Р	С			Co	olor		Tra	ınspareı	nt		ОК
	Testing	LED					C	CITIZEN	CLU-03	38-1205					
	The recommended size and power rating of the the source of the test, if it is required to be out actual conditions of the use environment					of range , the len	. Accord	ling to the distance of the di	he heat y tested	dissipati and tes	on capa	bility of	the la	mp and the	
4.Optic	FWHM						ı			ion curve	ı			_	
al index	angle			36. 2		35. 9	35. 7	36. 7	35. 2	35. 3	35. 5	36. 5		<u> </u>	
		K-value (CD/LM)													
	Effici	ency													
		See t	he signat	ure samp	le		`								
Compre e judg								Qualified							
Remarks: 1. Tool Number: V- Vernier Caliper 2D- Quadratic H-Height Gauge M-Tool Microscope P-Needle T- Thick Gauge R-Radius Gauge E-Visual. 2. Ambient temperature on the size of the product refer to the table on the right PC prod Length changes (mm) 0.6 0.4 0.2 0 0 0 0 0 0 0 0 0 0 0 0 0				duct siz	e chang	ges with		* - *	Size: Size: Size: Size: Size: Size: Size:	100mm 150mm 200mm 250mm					

Precautions:

- 1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.
- 2. Try to avoid touching the total reflection surface when taking the lens.
- 3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).
- 4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.



			Standard size	Upper Size limit	Lower size limi	Test result1	Test result2	Test result3	Test result4	Jud gme nt	Remarks		
	diameter		75			74. 99	74. 92	74. 92	74. 93		Test environment: In 20 °C -25 °C		
1.Size	heig	ht	35.1			35. 31	35. 28	35. 3	35. 26		environment to achieve thermal		
	thick	ness	2.5			2. 63	2.64	2.65	2.64		equilibrium after the test.		
				Gate shear can not affect the appearance of the lamp									
				See attachment "Appearance Inspection Standards"									
2.Appear	ance		See achment pearance	E		No burr	No burr	No burr	No bu	rr	OK		
Quality	In		spection andards"	_	1	No stains	No stains	No stains	No stai	ns	J. v.		
3.Materia	ıl			PC			Color	Tra	nsparent		OK		
	Testing	LED				CITI	ZEN CLU-0	38-1205					
	capability of the lamp FWHM angle K-value (CD/LM) Efficiency		angle 52.6 (-value CD/LM)			nment, the							
Compreh	nensiv		o oignate	o campio			(Qualified					
Remarks: 1. Tool Number: V- Vernier Caliper 2D- Quadratic H-Height Gauge M-Tool Microscope P-Needle T- Thick Gauge R-Radius Gauge E-Visual. 2. Ambient temperature on the size of the product refer to the table on the right PC Length 0.8 changes (mm) 0.6 0.2 0.2 0.1 0.8 0.8 0.9 0.9 0.9 0.9 0.9 0.9					ze change:	s with ten	→ S → S → S → S → S	ize: 5 ize: 00mm ize: 50mm	50mm 1				

Precautions:

- 1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.
- 2. Try to avoid touching the total reflection surface when taking the lens.
- 3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).
- 4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.



PI	N	HK-RG-75@35-15-D14-	-21-1g-1	Product Name	HK Moony 75@	2)35-15°	lens
Product	material	PC		Customer			
Package diagram		© □ Va	cuum packa	ge Bo	x package		~
Product	packing	6	A/ Box	4	pcs/Layer		
	. 3	4	Layer/Box	96	A/ Carton		
	NO.	Part No	Part name	Size	Dosage	Unit	Remarks
	1	2. 07. 0068	Blister box	23cm*21cm	16	BAG	
Dookogin	2	2. 08. 0001	PE film	30cm*30cm	16	PCS	
Packagin g Materials	3	2. 06. 0005	Reel label paper	6.2cm*8cm	16	PCS	
Materials	4	2. 06. 0005	Box label paper	6.2cm*9.2cm	1	PCS	
	5	2. 06. 0003	big plate	46.8cm*42.8cm	5	PCS	
	6	2. 06. 0018	big flat carton	48cm*44cm*19cr	m 1	PCS	
Remarks		The loose packing is not subje	ct to this specit	ïcation. Customer's	requirements shall	prevail	





Special notice


When gule pass through holes, columns and other structures, or part of the thin structure, will form a weld line. The product which uses multi-point injection welding line will appear because of the combination of sol, as shown below:


Syntneti



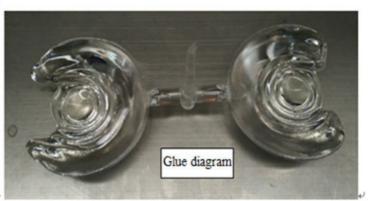

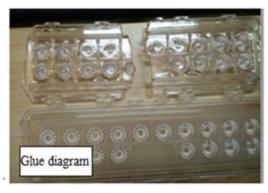

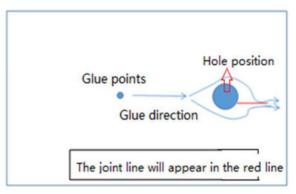

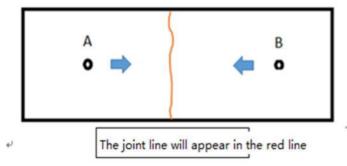

Please note:

The appearance of lines in the structure of the product as well as at the screw hole is a normal phenomenon, will not affect the actual use of the product, and can not be avoided at this stage.



Appearance inspection standards

1 Operating procedures

1.1.1Sampling standards, sampling plan and AQL

Test level: GB/T2828.1-2012The first part is according to the acceptance quality limit (AQL) retrieval batch inspection sampling plan, general inspection level Π level, CR class defect coefficient 0, MA defect rejection level AQL = 0.65, MI class defect rejection level AQL = 1.0; defect level please see 5.4.

2 Code table

Code	Code	Unit	Code	Code	Unit
	description			description	
N	Amount/pcs	pcs	D	Diameter	mm
L	Length	mm	Ħ	Depth	mm
W	Width	mm	DS	Distance	mm
S	Proportion	mm²	SS	Offset	mm

3 Test conditions

- 3.1 Sight distance and working hours: Sight distance should be 30-35cm, each side of the inspection time does not exceed 12s, the visual angle of 45-135 degrees;
- 3.2 Light: 2x40w cool white fluorescent lamp, the light source is 500-550mm away from the lens surface; in order to make the appearance defect can be correctly recognized, the illumination should be 500-1000Lux, and the observation time is 10 seconds.
 - 3.3 Visual inspection staff should be 1.0 (including corrected visual acuity) above, no color blindness, color weakness.

4 Appearance inspection standards

Test items	ludging standard	Inspection equipment	L Detect level		
restitems	Judging standard	Testing method	MI	MA	CR
	When start the machine and process, all products have to check the appearance of the sample, the appearance of the sample is divided into qualified samples and limited samples.				
Check the sample	1: Qualified sample refers to the appearance and structure standard of the product which recognized by the client, the sample size should be confirmed before mass production;	Sample comparison , visual			√

1		Ī	1	Ī	
	2: The limited sample refers to the limit of a particular exceptionally developed sample. Limit the sample only for its specific point of exception to confirm; The priority is higher than the other criteria in this table. When there is a limited sample, the limit sample shall prevail.				
Raw edge	Not allowed to affect the size and assembly	Visual, point card		√	
Scratch	1: Non-optical surface and non-exposed surface scratches should be visually insignificant and the length is less than 1/10 of the maximum surface size.	Visual, point card, calipers		√	
Fingerprint	Fingerprints are not allowed on all products	Visual		√	
Foreign objects, black spots, white spots	The product may not be attached to foreign objects, including oil, fiber, dregs of water gap and so on				√
Deformation	Insufficient filling shall not affect the appearance of the assembly and the exposed surfaces.	Visual, feeler			√
Poor ejection	Products may not appear bad ejection, including no convex top, thimble printed on the assembly surface shall not be higher than the product surface, non-assembled surface thimble height should not exceed the product size tolerances; thimble printing should be less than the product surface and no more than 0.3; thimble surface treatment should be consistent with the product side. Ejection strain: the optical surface and the appearance of the exposed surface after assembly are not allowed to have a strain, and the structural surface does not allow visual obvious strain.	Visual, point card		√	
Insufficient filling	Insufficient filling shall not affect the appearance of the assembly and the exposed surfaces, The signature sample shall prevail.	Visual, point card		√	
Shrink	When the entire surface of the product shrinks, the optical properties and dimensions must meet the requirements, and the visual will not significantly affect the appearance.Part shrink reference point defects	Visual, point card		√	
Flow marks、Welding line	 Product does not allow the presence of flow marks and welding lines unless the structure can not be avoided; The remaining flow marks shall not appear in the optical surface, a single L ≤ 10mm, no more than two 	Visual		✓	

Bubble	No bubbles are allowed	Visual		√	
Foreign objects, black spots, white spots	Not obvious or D ≤ 0.3mm black spots and foreign bodies in the area of 100x100mm not more than 1; Exceeded foreign matter black spots is judged bad.	Visual, point card	V		
Damaged	No damage is allowed	Visual			√
Cold glue	Optical surface may not have cold glue, non- optical surface cold glue should meet the visual is not obvious.	Visual	√		
	1: Do not affect the product size, shall not penetrate the optical surface, the cut should be smooth;				
Bad incision	2: Laser cutting products, the optical surface burns shall not occur after the processing is completed. Beading must not affect product installation	Visual			√
	3: Three molds and hot runner gate shall not appear residue.				
Scrub	Scrub surface should be uniform, off the scrub phenomenon should not be obvious, A single off scrub imprint requires D ≤ 1 mm and no more than 1 area within a 50x50 mm area	Visual		√	